

INTERNATIONAL STANDARD



**Organic light emitting diode (OLED) displays –
Part 5-3: Measuring methods of image sticking and lifetime**

IECNORM.COM : Click to view the full PDF of IEC 62341-5-3:2019 RLV



THIS PUBLICATION IS COPYRIGHT PROTECTED

Copyright © 2019 IEC, Geneva, Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either IEC or IEC's member National Committee in the country of the requester. If you have any questions about IEC copyright or have an enquiry about obtaining additional rights to this publication, please contact the address below or your local IEC member National Committee for further information.

IEC Central Office
3, rue de Varembe
CH-1211 Geneva 20
Switzerland

Tel.: +41 22 919 02 11
info@iec.ch
www.iec.ch

About the IEC

The International Electrotechnical Commission (IEC) is the leading global organization that prepares and publishes International Standards for all electrical, electronic and related technologies.

About IEC publications

The technical content of IEC publications is kept under constant review by the IEC. Please make sure that you have the latest edition, a corrigendum or an amendment might have been published.

IEC publications search - webstore.iec.ch/advsearchform

The advanced search enables to find IEC publications by a variety of criteria (reference number, text, technical committee,...). It also gives information on projects, replaced and withdrawn publications.

IEC Just Published - webstore.iec.ch/justpublished

Stay up to date on all new IEC publications. Just Published details all new publications released. Available online and once a month by email.

IEC Customer Service Centre - webstore.iec.ch/csc

If you wish to give us your feedback on this publication or need further assistance, please contact the Customer Service Centre: sales@iec.ch.

Electropedia - www.electropedia.org

The world's leading online dictionary on electrotechnology, containing more than 22 000 terminological entries in English and French, with equivalent terms in 16 additional languages. Also known as the International Electrotechnical Vocabulary (IEV) online.

IEC Glossary - std.iec.ch/glossary

67 000 electrotechnical terminology entries in English and French extracted from the Terms and Definitions clause of IEC publications issued since 2002. Some entries have been collected from earlier publications of IEC TC 37, 77, 86 and CISPR.

IECNORM.COM : Click to view the full text of IEC 60364-5-3:2019 PLV

INTERNATIONAL STANDARD



Organic light emitting diode (OLED) displays –
Part 5-3: Measuring methods of image sticking and lifetime

INTERNATIONAL
ELECTROTECHNICAL
COMMISSION

ICS 31.120; 31.260

ISBN 978-2-8322-7506-1

Warning! Make sure that you obtained this publication from an authorized distributor.

CONTENTS

FOREWORD	4
1 Scope	6
2 Normative references	6
3 Terms, definitions and abbreviated terms	6
3.1 Terms and definitions	6
3.2 Abbreviated terms	7
4 Measuring configuration	7
4.1 General	7
4.2 Light measuring device (LMD)	8
5 Standard measuring conditions	8
5.1 Standard measuring environmental conditions	8
5.2 Standard measuring darkroom conditions	8
5.3 Standard setup conditions	8
5.3.1 General	8
5.3.2 Adjustment of OLED display modules	9
5.3.3 Starting conditions of measurements	9
5.3.4 Test patterns	9
5.3.5 Conditions of measuring equipment	12
6 Measuring methods of image sticking	12
6.1 Purpose	12
6.2 Measuring method	12
6.2.1 Measuring equipment	12
6.2.2 Measuring procedure	13
6.3 Analysis and report	14
6.3.1 Analysis	14
6.3.2 Report	16
7 Measuring methods of the luminance lifetime	18
7.1 Purpose	18
7.2 Measuring method	18
7.2.1 Measuring equipment	18
7.2.2 Measuring procedure	19
7.2.3 Estimation of luminance lifetime	19
7.3 Analysis and report	19
Annex A (informative) Calculation method of equivalent signal level Calculating method for equivalent signal level to reflect the characteristics of the OLED display	24
A.1 Purpose	24
A.2 Determining the equivalent signal level	24
A.2.1 General	24
A.2.2 Calculation of the normalized luminance intensity	24
A.2.3 Extraction of the equivalent signal level from the IEC 62087:2011 10-min video loop Examples of extracted equivalent signal level	27
Annex (informative) Acceleration test of lifetime measurement	27
Annex B (informative) Colour difference with CIEDE2000	36
B.1 Purpose	36
B.2 Calculation of colour difference	36
Bibliography	37

Figure – Test pattern for image sticking
Figure – An example of the burn-in image
Figure – An example of Weibull distribution of lifetime
Figure – Accumulated colour intensity of IEC 62087:2011 10-min video loop in RGB subpixel format with equivalent signal distribution chart based on the left images, respectively
Figure – Accumulated colour intensity of the IEC 62087:2011 10-min video loop in W, R, G, and B format, with equivalent signal distribution chart based on the left images, respectively
Figure – Examples of Weibull distributions of accelerated lifetime test
Figure 1 – Measuring system and arrangement	7
Figure 2 – Test pattern for SDR displays	11
Figure 3 – Image sticking measuring area	11
Figure 4 – Test pattern for HDR displays	12
Figure 5 – Example of the resulting image after image stress	14
Figure 6 – Example of luminance behavior in operation for an OLED display panel or module	19
Figure 7 – Example of lifetime estimation with the extrapolation method	21
Figure 8 – Examples of estimated lifetime depending on the time elapsed	22
Figure A.1 – Measured 10 mA/cm ² to 80 mA/cm ² OLED degradation values and corresponding modelled functions with $m = 1 / 1,7$	25
Figure A.2 – Example of accumulated colour intensity of IEC 62087:2011 10-min video loop in RGB subpixel format with equivalent signal distribution chart based on the left images	30
Figure A.3 – Example of accumulated colour intensity of the IEC 62087:2011 10-min video loop in W, R, G, and B format, with equivalent signal distribution chart based on the left images	32
Table – An example of measuring distance and radius size
Table – An example of typical value
Table – An example of the image sticking time with reference
Table – An example of the image sticking data at target time
Table – Examples of lifetime measurement
Table – Summary of the acceleration test results in Figure B.1
Table – Statistical analysis results of the accelerated lifetime test in Figure B.1
Table 1 – Examples of maximum and average code value extracted from video samples	11
Table 2 – Information on test pattern	17
Table 3 – Example of typical value	17
Table 4 – Reporting format of the image sticking data at target time	18
Table 5 – Reporting format of the image sticking time with threshold	18
Table A.1 – Examples of the maximum and the minimum average equivalent signal levels (8 bits)	28

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ORGANIC LIGHT EMITTING DIODE (OLED) DISPLAYS –**Part 5-3: Measuring methods of image sticking and lifetime****FOREWORD**

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

This redline version of the official IEC Standard allows the user to identify the changes made to the previous edition. A vertical bar appears in the margin wherever a change has been made. Additions are in green text, deletions are in strikethrough red text.

International Standard IEC 62341-5-3 has been prepared by IEC technical committee 110: Electronic displays.

This second edition replaces the first edition published in 2013. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) the measurement vehicle for lifetime is only for the module;
- b) the measurement method for monitor or TV devices is modified;
- c) the digital signage display is included as an example of OLED devices;
- d) the measurement method with HDR (high dynamic range) for image sticking is added;
- e) the analysis method with CIEDE 2000 is added for image sticking;
- f) the information method for evaluating image sticking is modified.

The text of this standard is based on the following documents:

FDIS	Report on voting
110/1134/FDIS	110/1154/RVD

Full information on the voting for the approval on this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 62341 series, under the general title *Organic light emitting diode (OLED) displays*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed;
- withdrawn;
- replaced by a revised edition, or
- amended.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

ORGANIC LIGHT EMITTING DIODE (OLED) DISPLAYS –

Part 5-3: Measuring methods of image sticking and lifetime

1 Scope

This part of IEC 62341 specifies the standard ~~measurement conditions and measurement~~ measuring methods for determining the image sticking and lifetime of organic light emitting diode (OLED) display panels and modules, ~~except finalized display products for end customers, such as TV sets, monitor sets and mobile phones.~~ The measuring method for the lifetime mainly applies to modules.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

~~IEC 60050 (all parts), International Electrotechnical Vocabulary (available at <<http://www.electropedia.org>>)~~

IEC 60050-845, *International Electrotechnical Vocabulary (IEV) – Part 845: Lighting* (available at <<http://www.electropedia.org>>)

~~IEC 62087:2011, Methods of measurement for the power consumption of audio, video and related equipment~~

IEC 62341-1-2:2007, *Organic light emitting diode (OLED) displays – Part 1-2: Terminology and letter symbols*

IEC 62341-6-1:2009/2017, *Organic light emitting diode (OLED) displays – Part 6-1: Measuring methods of optical and electro-optical parameters*

~~IEC 61966-2-1:1999, Multimedia systems and equipment – Colour measurement and management – Part 2-1: Colour management – Default RGB colour space – sRGB~~

ISO 11664-1, *Colorimetry – Part 1: CIE standard colorimetric observers*

CIE 15:2004, *Colorimetry*

3 Terms, definitions and abbreviated terms

3.1 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC 62341-1-2:2007 and IEC 60050-845:1987 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>

- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1.1

equivalent current density

average current density of a certain pixel calculated from a varying luminance per frame image in a moving picture so that luminance degradation becomes similar at the same time

Note 1 to entry: See Annex A.

3.1.2

equivalent signal level

digital code value from 0 to 255 (in the case of 8 bits) transformed from the normalized luminance of a certain pixel by a ~~gamma~~ specified opto-electronic transfer function (OETF)

Note 1 to entry: See Annex A.

3.2 Abbreviated terms

For the purposes of this document, the following abbreviated terms apply:

APL	average picture level
CIELAB	CIE 1976(L*a*b*) colour space
DUT	devices under test
EOTF	electro-optical transfer function
FWHM	full-width-at-half-maximum
HDR	high dynamic range
LMD	light measuring device
OETF	opto-electronic transfer function
OLED	organic light emitting diode
PQ	perceptual quantizer
SDR	standard dynamic range

4 Measuring configuration

4.1 General

The system diagrams and/or operating conditions of the measuring equipment shall comply with the structure specified in each item. The measuring system and its arrangement are shown in Figure 1. The details are given in Clause 5.

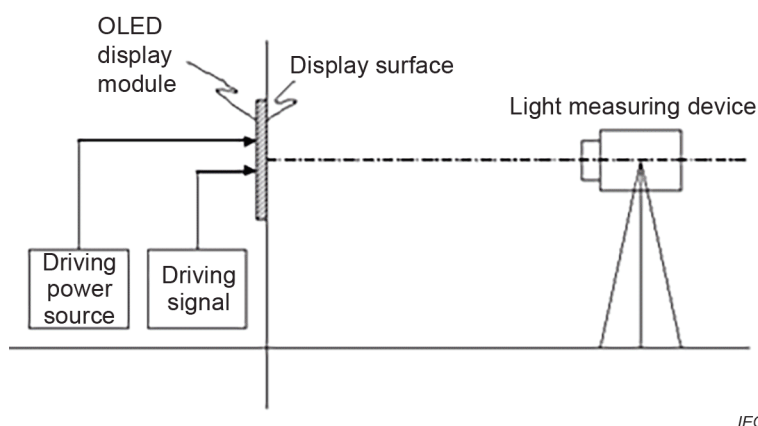


Figure 1 – Measuring system and arrangement

4.2 Light measuring device ~~(LMD)~~

~~The LMD as defined in IEC 62341-6-1:2009 shall be used. Specifically, the accuracy of the LMD at 1 degree of the measurement field angle is recommended as being $\leq \pm 3\%$, and with a repeatability $\leq \pm 0,5\%$.~~

The optical properties of displays shall generally be expressed in photometric or colorimetric units using the CIE 1931 standard colorimetric two-degree observer (see ISO 11664-1). Luminance can be measured by a photometer, and the CIE tristimulus values (X , Y , Z) or CIE chromaticity coordinates by a colorimeter. A spectroradiometer can also obtain photometric and colorimetric values through a numerical conversion of the measured spectral radiance data (see, for example, [1]¹). The following requirements are given for these instruments:

The LMD shall be a luminance meter, colorimeter, or a spectroradiometer. For DUTs that have sharp spectral peak full-width-at-half-maximums (FWHMs) smaller than 20 nm, a spectroradiometer should be used. A filter colorimeter should generally not be used for light sources with sharp spectral peaks. If they are used, the colorimeter shall be calibrated with a narrow bandwidth spectroradiometer to give the same results for the specific spectrum. Report the characteristics of the spectroradiometer which is used for calibration. For light sources with sharp spectral peaks, the maximum bandwidth of the spectroradiometer shall be ≤ 5 nm. The higher resolution spectroradiometer produces a more accurate colour measurement. In those cases, the wavelength accuracy shall be within $\pm 0,5$ nm. The spectroradiometer shall be capable of measuring spectral radiance over at least the 380 nm to 780 nm wavelength range, with a maximum bandwidth of 10 nm for smooth broadband spectra (i.e. broad spectrum with no sharp spikes).

Care shall be taken to ensure that the LMD has enough sensitivity and dynamic range to perform the required task. Before measuring the DUT, the LMD specification shall be checked.

5 Standard measuring conditions

5.1 Standard measuring environmental conditions

The standard measuring environmental conditions specified in IEC 62341-6-1:20092017, 5.1, shall be applied. For image sticking measurements, the environmental temperature shall be controlled at $25\text{ °C} \pm 2\text{ °C}$, otherwise a temperature-controlled detector shall be used. (The stability of the LMD shall be less than 1/5 of the intended detecting difference levels of luminance and colour.)

5.2 Standard measuring darkroom conditions

The standard measuring darkroom conditions specified in IEC 62341-6-1:20092017, 5.2, shall be applied.

5.3 Standard setup conditions

5.3.1 General

~~For the measurement area, the minimum radius for measurement with the distance and aperture angle is explained in Table 1.~~

¹ Numbers in square brackets refer to the Bibliography.

Table 1 — An example of measuring distance and radius size

Distance (mm)	Aperture angle (degree)	Radius of measurement field (mm)
500	2	10
	4	5
	0,2	4
	0,1	0,5

Standard setup conditions are given below. Any deviations from these conditions shall be recorded.

5.3.2 Adjustment of OLED display ~~modules~~

The adjustment of the OLED display ~~modules~~ specified in IEC 62341-6-1:2009/2017, 5.3.42, shall be applied.

5.3.3 Starting conditions of measurements

Warm-up time is defined as the time elapsed from the moment of switching on the supply voltage until repeated measurements of the display show a variation in luminance of less than 2 %/min. Repeated measurements shall be taken for a period of at least 15 min after starting. The luminance variations shall also not exceed 5 % during the total measurement.

5.3.4 Test patterns

The test patterns for display devices such as mobile phones, tablet PCs, monitors and TVs are shown in Figure 2. In the case of mobiles and tablet PCs, depending on the size of the OLED display panels or modules and measurement distance between the display and the LMD, if the pattern size is a smaller area than a 10 mm radius at a 500 mm measurement distance with a 2-degree aperture angle of the LMD, then the aperture angle of the LMD should be set to cover the pattern area as set in Table 1. The measuring distance and the aperture angle may be adjusted to achieve a measuring field greater than 500 pixels if the setting of the aperture angle is difficult. For all applications, the test pattern is used in Figure 2a), and usage method case for monitors and TVs such as Figure 2b) may be used. In order to get repeatability of measurement, the measuring location from P_0 to P_4 for TVs type as shown in Figure 2c) are set, considering the uniformity of the OLED display panels or modules.

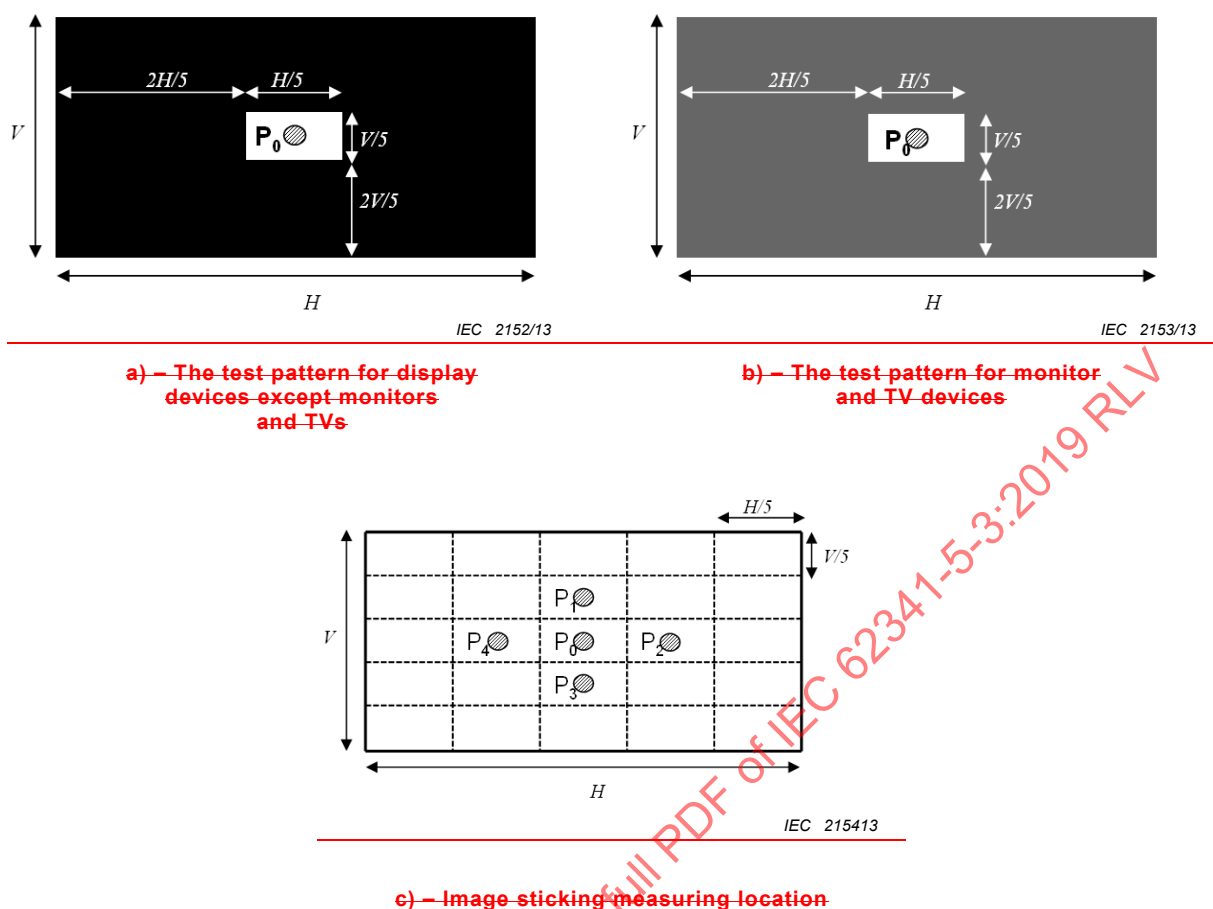


Figure 2 – Test pattern for image sticking

5.3.4.1 SDR displays

The test patterns for SDR display devices such as mobile phones, tablet PCs, monitors, TVs and digital signage are shown in Figure 2. The test pattern for SDR displays is divided into two groups.

1) Test pattern for mobiles and tablet PC displays

In the case of mobiles and tablet PCs, the measurement distance between the display and the LMD depends on the size of the OLED display panels or modules. The measuring distance and the aperture angle may be adjusted to achieve a measuring field greater than 500 pixels if the setting of the measurement field angle is not applied. For display devices except monitors, TVs and digital signage, the test pattern with a white level at the 4 % window box located in the centre and a black level in the background, is used in Figure 2a).

2) Test pattern for monitors, TVs and digital signage displays

For monitors, TVs and digital signage, the test pattern is extracted by video analysis to reflect the characteristics of the video sample. For the test pattern, the maximum code value is allocated at the 4 % window box in the centre and the average code value is in the background. The examples of the maximum and average gray code values are shown in Table 1. The example of the test pattern is shown in Figure 2b). The maximum and average code values between 0 and 255 (in the case of 8 bits) could be extracted from the accumulating image for all frames of the video sample, which is converted as equivalent grayscale from each colour channel.

NOTE 1 Image sticking is influenced by the characteristics of the OLED displays [5], [7]. Some manufacturers of OLED displays apply various algorithms to optimize the quality of each device, and this also influences the image

sticking. To consider the characteristics of an OLED display, the method in Annex A is used for the test pattern reflecting the characteristics of the OLED display.

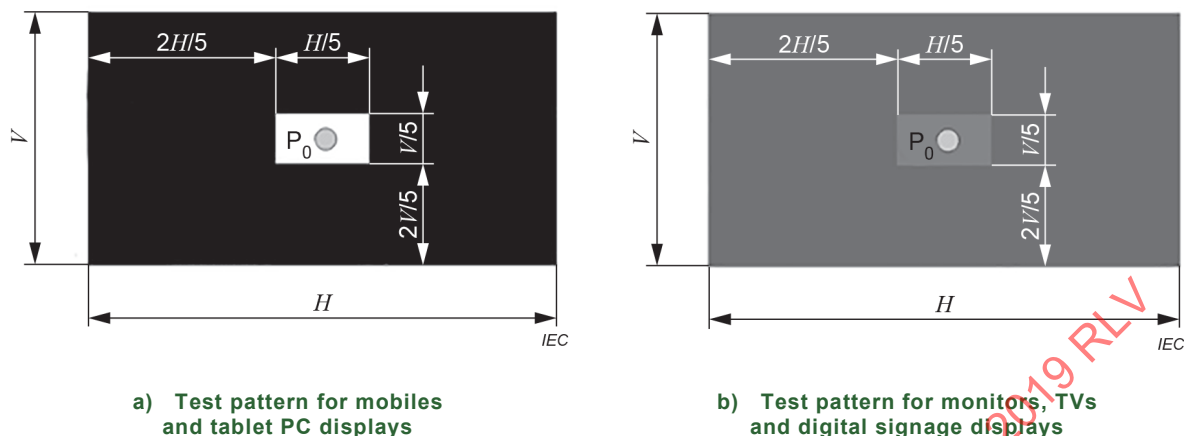


Figure 2 – Test pattern for SDR displays

Table 1 – Examples of maximum and average code value extracted from video samples

Examples of test video	Maximum code value	Average code value
IEC 62087:2011	107	84
Broadcast video sample	183	102

NOTE 2 For the test pattern, any video samples could be selected as needed. Table 1 shows two kinds of representative examples. The broadcast video sample example is constructed by considering the viewing ratio of the content of TV programmes based on the Korea broadcast media use environmental survey report: entertainment (30,9%), news (20,2 %), drama (16,8 %), and so on [4]. The average gray level and test pattern size are different between SDR and HDR in TVs. Depending on the purpose of the test, Figure 2b) or Figure 4a) would apply.

3) Measuring area

In order to get repeatability of measurement, the measuring area from P_0 to P_4 for displays is set to consider the uniformity of the OLED display panels or modules, as shown in Figure 3. If the centre window size is changed, then it should be reported in Table 2.

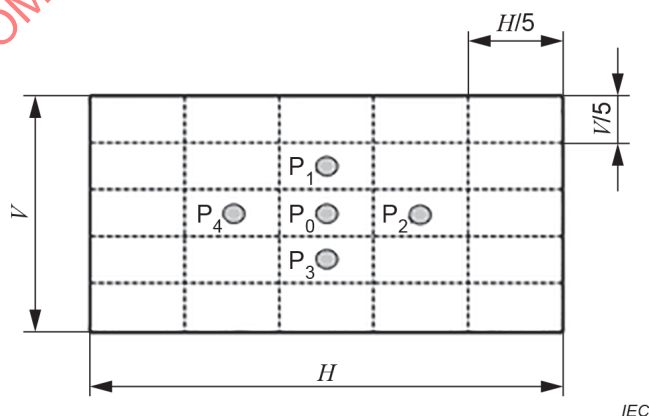


Figure 3 – Image sticking measuring area

4) Checking the test pattern

For SDR displays, the output luminance can be different although they have the same digital code value inputs. To check the brief information of the selected test pattern, the output luminance for the test pattern should be measured and reported.

Apply the test pattern on OLED displays and measure the output luminance on the measuring area from P_0 to P_4 as shown in Figure 3. The results of the output luminance of the test pattern should be reported in Table 2.

5.3.4.2 HDR displays

In 5.3.4.1, the test pattern for SDR displays is described. The test pattern for HDR displays is shown in Figure 4a). It is based on the PQ curve and 10 bits. The test pattern for HDR displays is proposed separately because the characteristics of the contents of the SDR and HDR are different. The test pattern for SDR or HDR can be used as needed. The background code value should be 510. The size of the box window should be 10 %, which is located in the centre. The code value of the 10 % box window should be 710. The measured luminance of the box window and the background luminance should be reported. To get repeatability of the measurement data, the measuring area from P_0 to P_4 is the centre of the boxes, as shown in Figure 4b). The measurement data should be reported in Table 2.

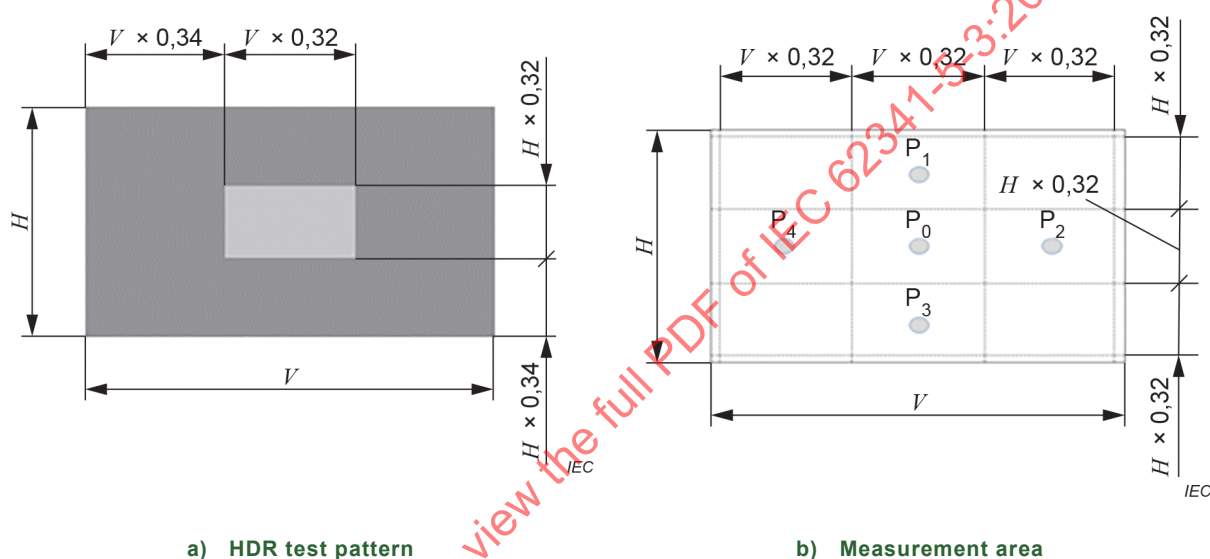


Figure 4 – Test pattern for HDR displays

NOTE The code value of the 10 % box window and background is the result of the analysed data of HDR contents which are HDR games, drama and documentary.

5.3.5 Conditions of measuring equipment

The general conditions in IEC 62341-6-1:20092017, Clause 5, shall be applied.

6 Measuring methods of image sticking

6.1 Purpose

The purpose of this method is to measure the image sticking of an OLED display ~~panels or modules~~.

6.2 Measuring method

6.2.1 Measuring equipment

The following equipment defined in IEC 62341-6-1:20092017, ~~6.1.2~~ 5.3.4, shall be used:

- a) power supplies and signal sources for driving,
- b) LMD.

6.2.2 Measuring procedure

The OLED display ~~modules~~ shall be set in darkroom conditions for measurement.

a) Initial measurements on full screen pattern

Apply a full white screen driving signal to the OLED display ~~modules over the full screen~~, and set all power supplies to the standard operation conditions. ~~However, for some display applications, the full screen luminance can be reduced, according to 7.3.1 of IEC 62341-6-4:2009.~~

Measure the initial spectral radiance or tristimulus values ~~of white~~ at P_0 to P_4 as shown in Figure ~~2c) 3~~. The initial spectra radiance or tristimulus values of the primary colours may also be measured individually.

b) Image ~~burn-in~~ stress using the test pattern

~~For the test pattern for display devices (except monitors and TVs), set the test input signal to the OLED display modules to generate a 0 % luminance level over the full screen and a peak luminance at the test pattern which is located at the centre of the display as shown in Figure 2a). For monitor and TV, set the peak luminance level over the 4 % window pattern located in the centre of the display with a 15 % luminance level of the peak luminance over the background area. For information about guidance, see Annex C of IEC 62087:2011. If the other pattern is used, it should be based on Annex A of this document and reported.~~

For image stress, the test pattern based on 5.3.4 for display devices should be applied to the OLED display.


Keep the test pattern until the specified time, considering the luminance degradation curve. For example, the measurement time can be every 1 h during the first 6 h, and every 24 h during the first 120 h, then every 72 h until the target time in the standard measurement condition. Alternatively keep the test pattern until the target time in the standard measurement condition.

c) Measurements on full screen pattern after image stress

Before the measurement, turn off the OLED display and stabilize it to the standard operation condition. Then turn on the OLED display again and apply a full white screen driving signal to the OLED display ~~modules~~ over the full screen. Set all power supplies also to the standard operation conditions. Measure the spectral radiance or the tristimulus values at the same measuring location as the initial measurement. The initial and final spectra radiance or tristimulus values of the individual primary colours may also be measured and reported.

For the measurement method, only white tone is considered. For the other primary colours such as red, green and blue, each test pattern should be designed following the methods of 5.3.4, and each full primary colour screen pattern should be used for measurement.

All measurements shall be done at the target time of ~~400 and~~ 500 h and shall be reported. In Figure ~~3 5~~, an example of ~~the burn-in~~ image stress is shown.

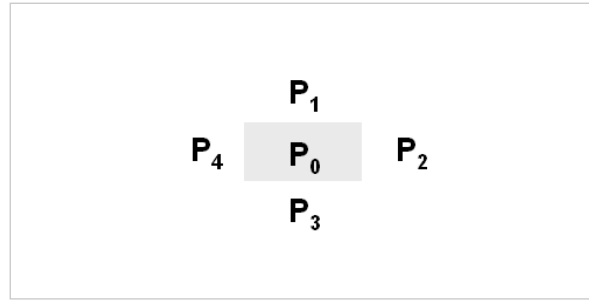

IEC 2155/13

Figure 3 — An example of the burn-in image

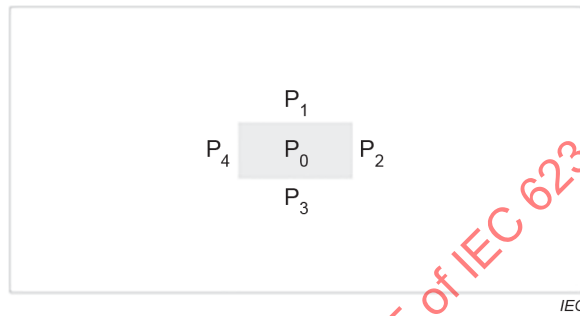


Figure 5 – Example of the resulting image after image stress

6.3 Analysis and report

6.3.1 Analysis

6.3.1.1 Luminance and chromatic deviation method

Image sticking can be characterized by luminance and chromatic deviation.

The image sticking of luminance $IS(t)$ for white is calculated as follows:

$$IS(t) = \left| 1 - \frac{\sum_{i=1}^4 L_i(t) / L_0(t)}{\sum_{i=1}^4 L_i(t_0) / L_0(t_0)} \right| \times 100 (\%) \quad (1)$$

where

t is the specified measurement time;

t_0 is the initial measurement time;

L_i is the luminance of the measurement location from P_i .

Chromatic deviation $\Delta u'v'(t)_0$ caused by image sticking at P_0 over time for white is calculated as follows:

$$\Delta u'v'(t)_0 = \sqrt{\{u'(t) - u'(t_0)\}^2 + \{v'(t) - v'(t_0)\}^2} \quad (2)$$

where

t is the specified measurement time;
 t_0 is the initial measurement time;
 $(u'(t), v'(t))$ is the white chromaticity value at the specified time;
 $(u'(t_0), v'(t_0))$ is the white chromaticity value at the initial time.

The average of the chromatic deviation $\Delta u'v'(t)_{\text{AVG}}$ caused by image sticking between different measuring locations from P_1 to P_4 for white is calculated as follows:

$$\Delta u'v'(t)_{\text{AVG}} = \left(\sum_{i=1}^4 \sqrt{\{u'_i(t) - u'_0(t)\}^2 + \{v'_i(t) - v'_0(t)\}^2} \right) / 4 \quad (3)$$

where

t is the specified measurement time;
 $(u'_i(t), v'_i(t))$ are the chromaticity coordinates of the measuring locations of P_i ($i = 1, 2, 3, 4$).

The value of u' and v' can be calculated from the tristimulus value X , Y , and Z using the following formula:

$$\begin{aligned} u' &= 4X / (X + 15Y + 3Z) \\ v' &= 9Y / (X + 15Y + 3Z) \end{aligned} \quad (4)$$

6.3.1.2 Colour difference method

6.3.1.2.1 General

The image sticking shall be analyzed with ΔE^*_{ab} of the three-dimensional, CIE 1976 $L^*a^*b^*$ colour space (see CIE 15-2004) following the procedure in 6.2.2. Additional three-dimensional uniform-colour spaces and colour spaces may also be used and identified in the test report. Each colour point can be plotted on the L^* , a^* , and b^* axes of the CIE $L^*a^*b^*$ colour space by referencing the peak white tristimulus value (X_n , Y_n , Z_n) in the measuring location P_0 at the initial time t_0 and using the following transformation formula:

$$\begin{aligned} L^*_i(t) &= 116 \times f(Y_i(t)/Y_n) - 16 \\ a^*_i(t) &= 500 \times [f(X_i(t)/X_n) - f(Y_i(t)/Y_n)] \\ b^*_i(t) &= 200 \times [f(Y_i(t)/Y_n) - f(Z_i(t)/Z_n)] \end{aligned} \quad (5)$$

where

$$f(x) = \begin{cases} x^{1/3} & x > (6/29)^3 \\ \frac{1}{3} \left(\frac{29}{6} \right)^2 x + \frac{4}{29} & \text{otherwise} \end{cases}$$

t is the specified measurement time;

L^*_i, a^*_i, b^*_i is the CIELAB colour coordinates of the measuring locations of P_i ($i = 0, 1, 2, 3, 4$);

(X_n, Y_n, Z_n) is the tristimulus value of the reference white in the measuring location P_0 at the initial time t_0 .

6.3.1.2.2 CIE 1976

The colour difference formula $\Delta E^*_{\text{ab}}(t)_0$ caused by image sticking at P_0 over time for white is calculated as follows:

$$\Delta E_{ab}^*(t)_0 = \sqrt{\{L_0^*(t) - L_0^*(t_0)\}^2 + \{a_0^*(t) - a_0^*(t_0)\}^2 + \{b_0^*(t) - b_0^*(t_0)\}^2} \quad (6)$$

where

t is the specified measurement time;

t_0 is the initial measurement time;

L_0^*, a_0^*, b_0^* are the CIELAB colour coordinates of the measuring locations of P_0 .

The average of the colour difference formula $\Delta E_{ab}^*(t)_{AVG}$ caused by image sticking between different measuring locations from P_1 to P_4 for white is calculated as follows:

$$\Delta E_{ab}^*(t)_{AVG} = \left(\sum_{i=1}^4 \sqrt{\{L_i^*(t) - L_0^*(t_0)\}^2 + \{a_i^*(t) - a_0^*(t_0)\}^2 + \{b_i^*(t) - b_0^*(t_0)\}^2} \right) / 4 \quad (7)$$

where

t is the specified measurement time;

L_i^*, a_i^*, b_i^* are the chromaticity coordinates of the measuring locations of P_i ($i = 1, 2, 3, 4$).

6.3.2 Report

6.3.2.1 General

The typical value of image sticking can be reported with specified time, as shown in Table 2. If other primary colours are used such as red, green and blue, it should be reported.

Table 2 — An example of typical value

time (hour)	Colour	Measurement data					
		P_0			Average of $P_1 \sim P_4$		
		X	Y	Z	X	Y	Z
0	White						
1	White						

6.3.2.2 Image sticking time

The estimated time of image sticking can be reported with the result of the comparison between the reference luminance ratio, the chromatic deviation, and the colour difference, as shown in Table 3.

Table 3 — An example of the image sticking time with reference

Factor	Threshold	Estimated time
Luminance ratio (IS)	3 %	
Chromatic deviation $\Delta u', v'(t)_0$ at P_0	0,004	
Average of chromatic deviation $\Delta u', v'(t)_{AVG}$		
Colour difference $\Delta E_{ab}^*(t)_0$ at P_0	5	
Average of colour difference $\Delta E_{ab}^*(t)_{AVG}$		

6.3.2.3 Image sticking data

The image sticking can be reported after target time, as shown in Table 4.

Table 4 — An example of the image sticking data at target time

Time (hours)	Factor	Result data
400	Luminance ratio (IS)	
	Chromatic deviation $\Delta u'v'(t)_0$ at P_0	
	Average of chromatic deviation $\Delta u'v'(t)_{AVG}$	
	Colour difference $\Delta E^*_{ab}(t)_0$ at P_0	
	Average of colour difference $\Delta E^*_{ab}(t)_{AVG}$	

6.3.2.1 Information of test pattern

Before reporting the measurement data, information on the used test pattern should be reported, as shown in Table 2. It includes the type of test pattern, the size of the window box, the allocated code values located at the centre and background, and the output luminance of OLED displays for the test pattern. If other test patterns not listed in 5.3.4 are used, they should be reported in accordance with Table 2.

Table 2 – Information on test pattern

Types of test pattern		(SDR, HDR, etc.)
Size of window box		- %
Code value	Centre	– (based on 8 or 10 bits)
	Background	– (based on 8 or 10 bits)
Output luminance	Centre	(P_0)
	Background	(average of from P_1 to P_4)

6.3.2.2 Measurement data record

The typical value of image sticking can be reported following the format shown in Table 3. For the typical value, the initial data should be reported and other data at the specified time can be selected following the measuring procedure of image stress.

Table 3 – Example of typical value

Time (hour)	Colour	Measurement data					
		P_0			Average of P_1 to P_4		
		X	Y	Z	X	Y	Z
0	White						
1	White						
⋮	White						

6.3.2.3 Image sticking data

Image sticking should be reported with the result of the comparison between the reference luminance ratio, the chromatic deviation, and the colour difference, following the format shown in Table 4. Each result data should be calculated from Formulae (1) to (7), and should

be reported in Table 4. The designated time is 500 h. If the time is changed, it should be reported.

Table 4 – Reporting format of the image sticking data at target time

Time (hours)	Factor	Result data
500	Luminance ratio (IS)	
	Chromatic deviation $\Delta u'v'(t)_0$ at P_0	
	Average of chromatic deviation $\Delta u'v'(t)_{AVG}$	
	Colour difference $\Delta E^*_{ab}(t)_0$ at P_0	
	Average of colour difference $\Delta E^*_{ab}(t)_{AVG}$	

It is recommended to refer to ΔE^*_{00} using the method in Annex B, if it is necessary to calculate the colour difference with CIEDE2000 instead of ΔE^*_{ab} .

6.3.2.4 Image sticking time

Image sticking can also be reported as the estimated time with the thresholds as shown in Table 5. The thresholds of the image sticking can be set depending on the display size, peak luminance and so on. They can be selected as needed and should be reported.

Table 5 – Reporting format of the image sticking time with threshold

Factor	Threshold	Estimated time
Luminance ratio (IS)	-	
Chromatic deviation $\Delta u'v'(t)_0$ at P_0	-	
Average of chromatic deviation $\Delta u'v'(t)_{AVG}$		
Colour difference $\Delta E^*_{ab}(t)_0$ at P_0	-	
Average of colour difference $\Delta E^*_{ab}(t)_{AVG}$		

It is recommended to refer to ΔE^*_{00} using the method in Annex B, if it is necessary to calculate colour difference with CIEDE2000 instead of ΔE^*_{ab} .

7 Measuring methods of the luminance lifetime

7.1 Purpose

The purpose of this method is to measure the luminance lifetime of the OLED display ~~panels~~ ~~or~~ modules. The lifetime is the elapsed time required for the luminance to decrease to the specified fraction of the initial luminance set in operation. Unless otherwise specified, half luminance lifetime shall be used for lifetime measurements. When describing the lifetime, the initial luminance, the evaluation temperature and degradation ratio shall be specified.

7.2 Measuring method

7.2.1 Measuring equipment

The following equipment shall be used:

- power supplies and signal sources for driving,
- LMD.

7.2.2 Measuring procedure

The OLED display ~~panels or modules~~ shall be set in the standard measuring conditions. The darkroom conditions shall be applied when the luminance is measured. Apply a full white screen driving signal to the OLED display ~~panel or module~~ at 100 % gray level, and set all power supplies to the standard operation conditions. However, for some display applications, the full screen luminance can be reduced, according to ~~7.3.1 of IEC 62341-6-1:2009~~ 2017, 6.3.

Measure the initial luminance, keep the above operating conditions and measure the luminance of the ~~device under test (DUT)~~ at the specified time. The specified time can be (1, 2, 5, 10, 20, 50, 100, 200, 500, 1 000 and 2 000) days. In Figure 6, an example of the luminance behavior in operation is shown. When measuring the luminance lifetime, an acceleration method ~~may~~ can be acceptable (see ~~Annex B A.2.2~~). If an acceleration method is applied, the acceleration condition, the acceleration ratio and the theoretical basis of the method shall be reported.

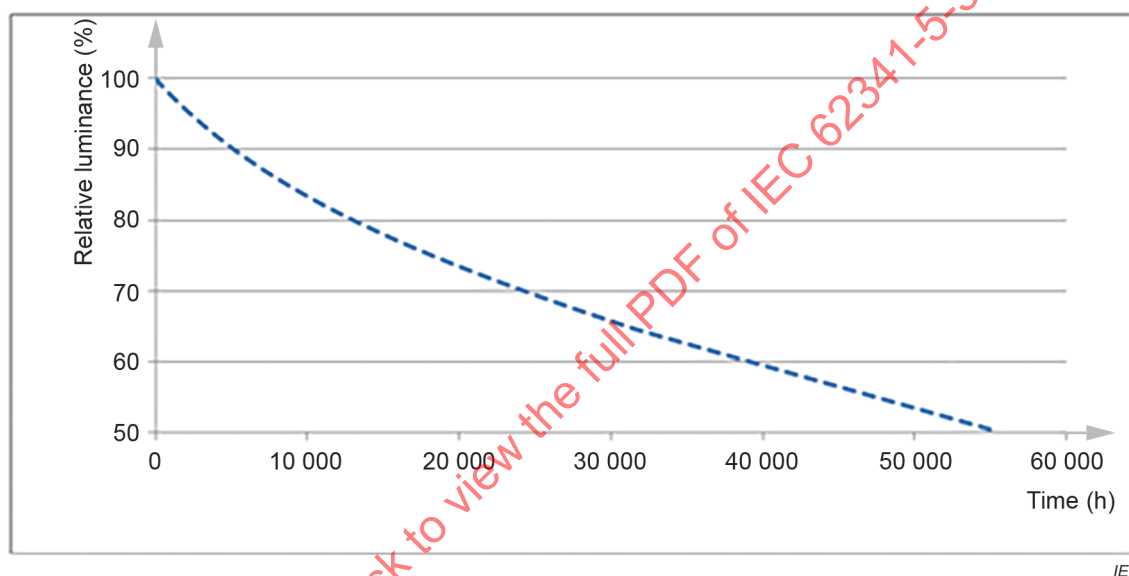


Figure 6 – Example of luminance behavior in operation for an OLED display ~~panel or~~ module

7.2.3 Estimation of luminance lifetime

The direct measurement of luminance lifetime would typically take an impractically long time, exceeding several tens of thousands of hours of panel operation. Extrapolation methods are applied to shorten the measuring period. Luminance lifetime is a degradation phenomenon of the light emission from OLED displays. An extrapolation method can be applied to estimate the lifetime by using a formula which models the degradation with time. This method is based on the knowledge of the degradation phenomenon.

~~The degradation phenomenon shows exponential degradation as follows [1]²:~~

$$L(t) = L(0) \exp \left[- \left(\frac{t}{a} \right)^{1/n} \right] \quad (8)$$

²—Numbers in square brackets refer to the Bibliography.

where

t is the operating time;

$L(t)$ is the luminance value of the degradation phenomena at time t ;

$L(0)$ is the initial luminance value of $L(t)$;

a is the constant (relaxation time);

n is the acceleration factor.

However, in the case of luminance degradation of OLED displays, this formula does not coincide with the observed result. Other formulae should be chosen.

In Equation (9), there is a linear relation between $\ln(L(0)/L(t))$ and $\ln(t)$.

$$\ln[\ln(L(0)/L(t))] = 1/n \ln(t) - 1/n \ln(a) \quad (9)$$

The degradation phenomenon shows exponential degradation as follows [16]:

$$L(t) = L(0) \exp \left[- \left(\frac{t}{a} \right)^\beta \right] \quad (10)$$

where

t is the operating time;

$L(t)$ is the luminance value of the degradation phenomena at time t ;

$L(0)$ is the initial luminance value of $L(t)$;

a is the constant (relaxation time);

β is the coefficient.

In Formula (11), there is a linear relation between $\log [\ln (L(0)/L(t))]$ and $\log (t)$.

$$\log [\ln (L(0) / L(t))] = \beta \log (t) - \beta \log (a) \quad (11)$$

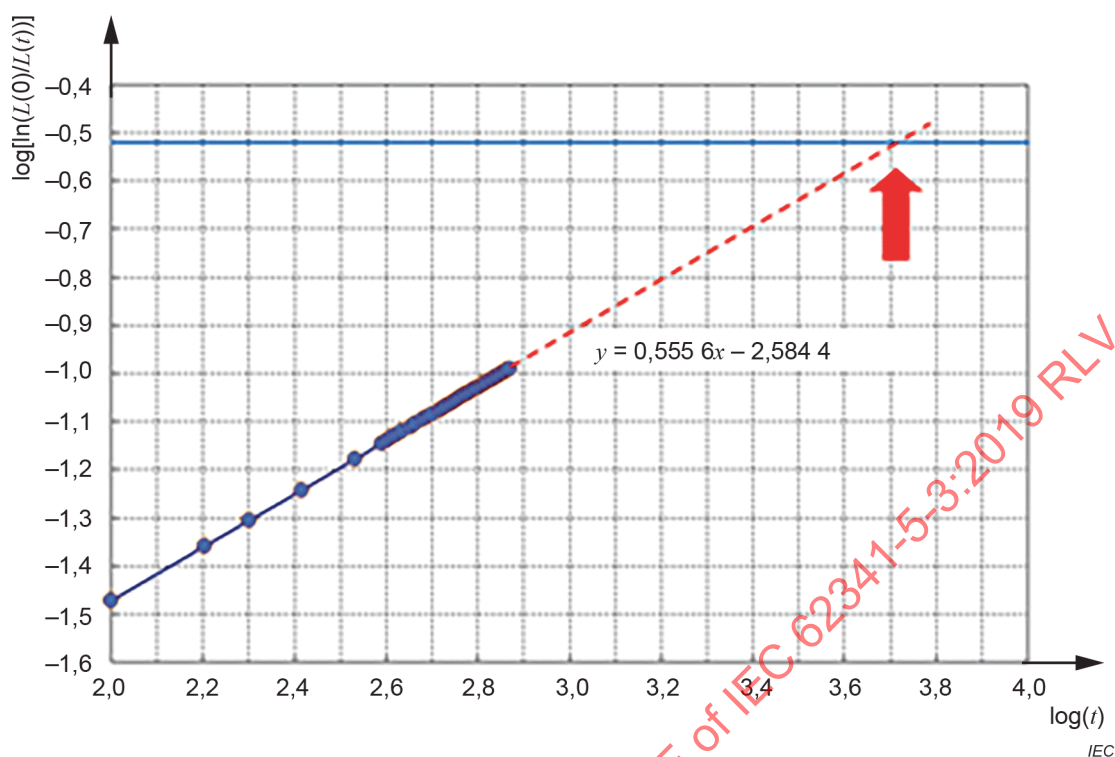


Figure 7 – Example of lifetime estimation with the extrapolation method

With the linear relation, the lifetime ~~may~~ can be estimated, using the extrapolation method (Figure 7). For example, the formula $y = 0,555\ 6x - 2,584\ 4$ is defined based on the real measurement data. y could be -0,541 47 by calculating $\log [\ln (L(0)/(0,75 \times L(0)))]$. After calculating the formula to get the time, it is possible to estimate the life time which is about 4 753 h where $L(t)$ is 0,75 times $L(0)$. To check the suitability of the degradation formula, the drift of the estimated lifetime should be used. If the formula is appropriate, there will be no significant drift of the estimated value with the driven time. Examples are shown in Figure 8.

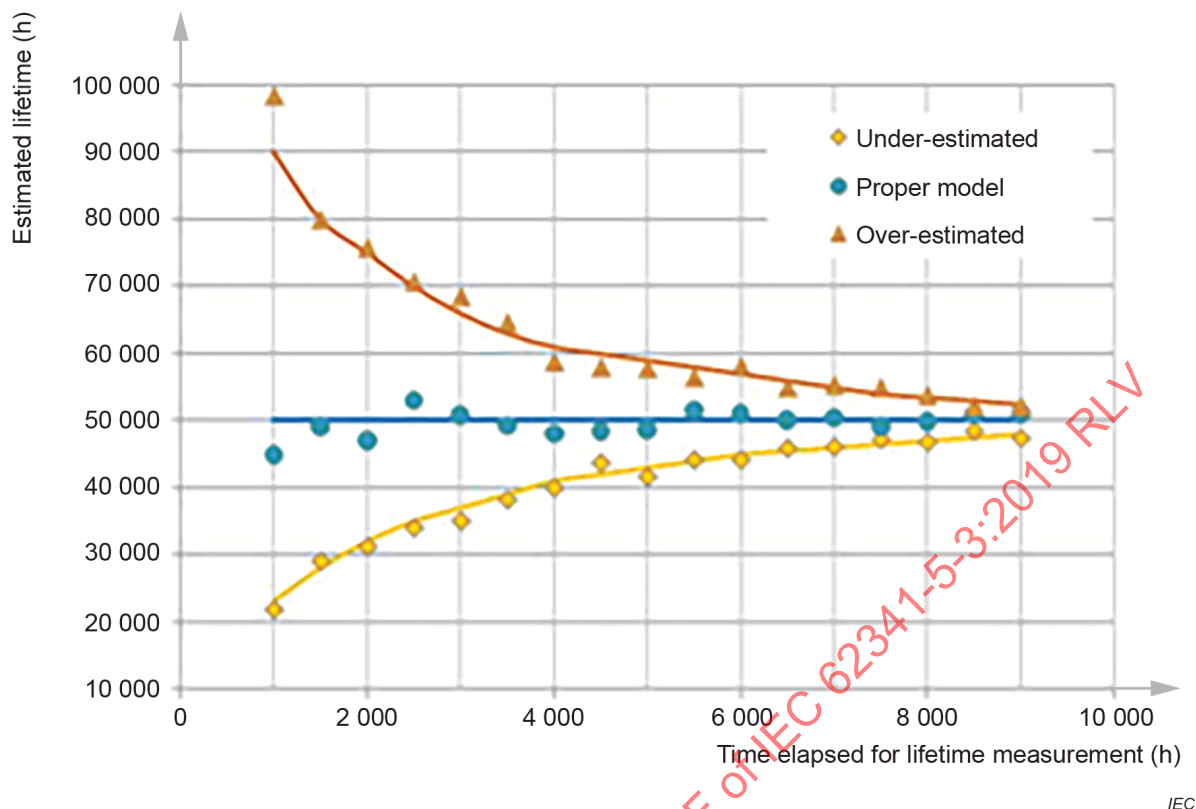


Figure 8 – Examples of estimated lifetime depending on the time elapsed

7.3 Analysis and report

Generally, the lifetime follows the Weibull distribution, and the lifetime can be expressed with statistical parameters which represent the Weibull distribution.

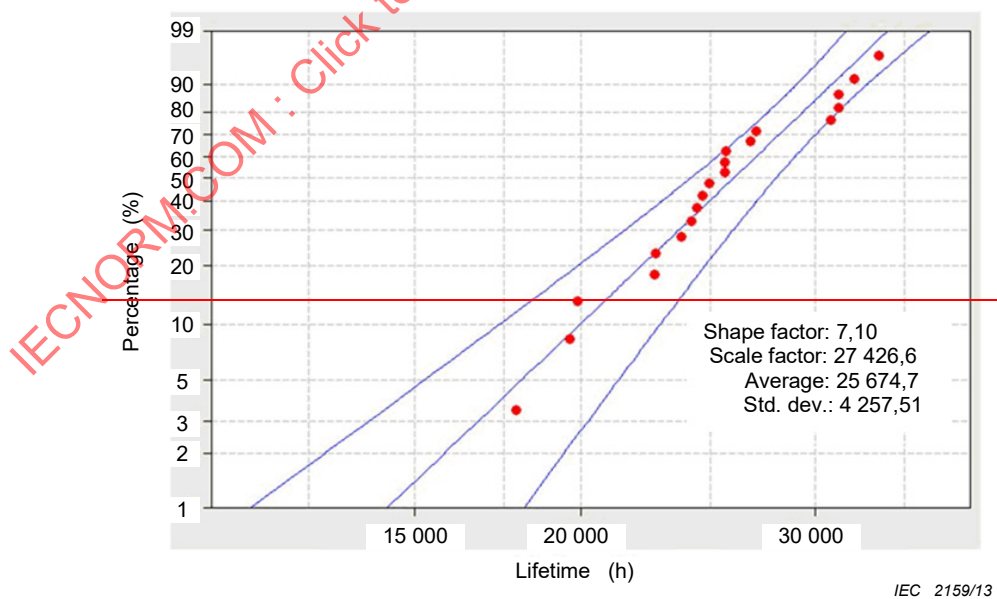


Figure 7 – An example of Weibull distribution of lifetime

The typical value and deviation should be reported for the lifetime. The typical value of the lifetime can be reported with the average mean time to failure (MTTF) or scale factor of the Weibull distribution, and the deviation can be reported with the standard deviation or shape

factor of the Weibull distribution. Furthermore, the lifetime may be reported with the value at the lower 10 % position (B_{10}) in the Weibull distribution [2] (see Table 5).

Table 5 – Examples of lifetime measurement

Items		Data
Number of samples		20
Typical values	MTTF	25 674
	Scale factor	27 427
Deviations	Standard deviation	4 258
	Shape factor	7,10
B_{10}		19 977

Annex A (informative)

~~Calculation method of equivalent signal level~~ Calculating method for equivalent signal level to reflect the characteristics of the OLED display

A.1 Purpose

The purpose of this method is to define the procedure for calculating the equivalent signal level for the image sticking of ~~a TV type~~ monitors, TVs, or digital signage devices using video samples. Through the calculation of the equivalent signal level, the characteristics of the OLED display can be reflected.

A.2 Determining the equivalent signal level

A.2.1 General

Since OLED degradation is generally not proportional to current density, the quantities of normalized luminance intensity and equivalent current density, which are proportional to OLED degradation, are defined [6]. It is possible to apply this quantity to the usage model-based image sticking measuring method. The normalized luminance intensity is in the RGB linear space and can be converted to the equivalent signal level to apply linear to non-linear conversion. Further, accurate image sticking simulation for a specific application can be achieved by computing one image in terms of normalized luminance intensity or equivalent current density of various kinds of the actual usage images and image sources.

A.2.2 Calculation of the normalized luminance intensity

The equivalent current density is calculated using the OLED degradation function. The OLED degradation function that is normalized by initial luminance is given empirically by the stretched exponential function:

$$\frac{L(t)}{L(0)} \propto A \exp(-KJt^m) \quad (\text{A.1})$$

where $L(0)$ is the initial luminance, A , K and m are fitting coefficients depending on the device, J is the current density of the OLED device in subpixel, and t is the time of the test duration. K and m are determined from the measurement data. ~~$m=1/n$, n is the acceleration factor according to Equations (8) and (9).~~ $m = \beta$: β is the coefficient according to Formula (10) and Formula (11). Figure A.1 shows the measured luminance degradations and fitted lines according to Formula (A.1).

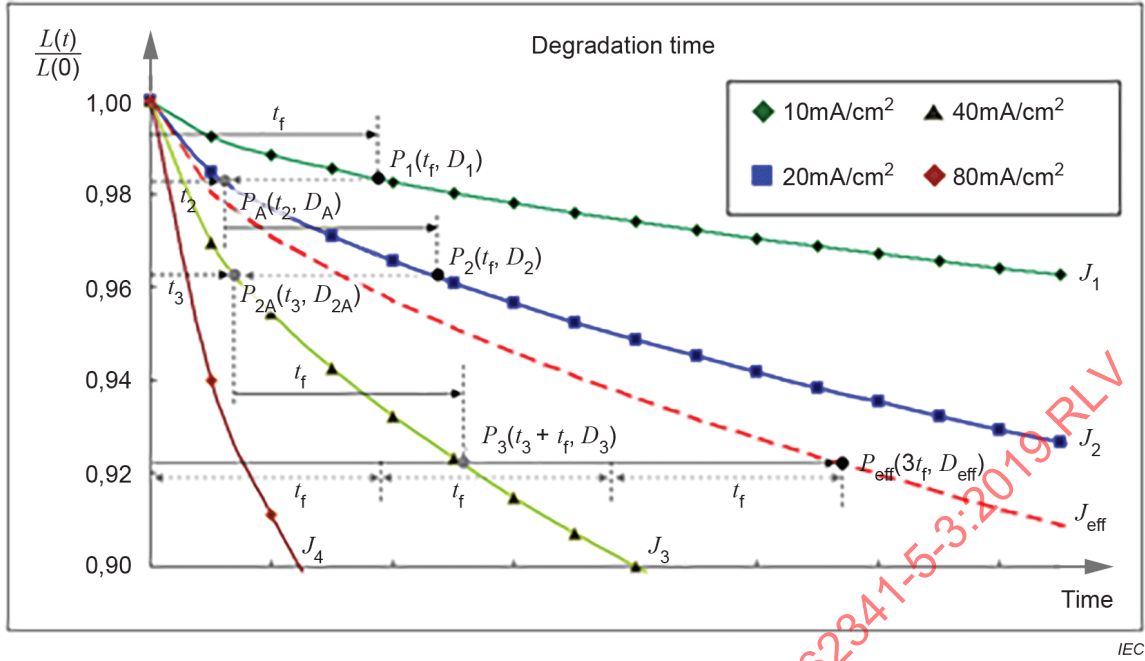


Figure A.1 – Measured 10 mA/cm² to 80 mA/cm² OLED degradation values and corresponding modelled functions with $m = 1 / 1,7$

As shown in Figure A.1, this model accurately accounts for the degradation of the OLED as a function of both time and current density for a typical OLED. By applying this model and assuming that degradation is additive, one can derive a degradation function for a subpixel which is degraded by exposure to multiple current densities over time. Therefore, D_n , which is the degradation of a pixel by the temporal sequence of current densities $J_1, J_2, J_3 \dots J_n$ and N over a time period t_f is defined. D_n is calculated as follows.

- a) Consider a first degradation of an OLED, resulting from exposure to current density J_1 over a time period t_f . This degradation is expressed as:

$$D_1 = A \exp(-K J_1 t_f^m) \quad (\text{A.2})$$

- b) Consider an alternative degradation D_A of an OLED resulting from current density J_2 over a time period t_2 . This degradation is expressed as:

$$D_A = A \exp(-K J_2 t_2^m) \quad (\text{A.3})$$

t_2 can now be defined, such that it is the time required to make D_1 equal to D_A . Accordingly t_2 can be calculated from Formula (A.2) and Formula (A.3), and is expressed as:

$$t_2 = \left(J_1 / J_2 \right)^{1/m} t_f \quad (\text{A.4})$$

Using Formula (A.4), time period t_2 can be scaled to account for differences between current densities J_1 and J_2 . Therefore, after an OLED is exposed to J_1 for a first time period and J_2 for a second time period, the resulting degradation can be expressed as:

$$D_2 = A \exp(-K J_2 (t_2 + t_f)^m) = A \exp\left(-K \left(\frac{J_1^{1/m} + J_2^{1/m}}{2}\right)^m (2t_f)^m\right) \quad (\text{A.5})$$

- c) Consider the degradation of an OLED over a third time interval t_3 with exposure to current density J_3 . Degradation D_{2A} can then be expressed as:

$$D_{2A} = A \exp(-K J_3 t_3^m) \quad (\text{A.6})$$

Again, defining t_3 such that it is the time required to make D_2 and D_{2A} equal, t_3 is calculated from Formula (A.5) and Formula (A.6) and is expressed as:

$$t_3 = \left(\frac{J_1^{1/m} + J_2^{1/m}}{2}\right) \frac{1}{J_3^{1/m}} (2t_f) \quad (\text{A.7})$$

Therefore, after the third time interval, the degradation D_3 is expressed as:

$$D_3 = A \exp(-K J_3 (t_3 + t_f)^m) = A \exp\left(-K \left(\frac{J_1^{1/m} + J_2^{1/m} + J_3^{1/m}}{3}\right)^m (3t_f)^m\right) \quad (\text{A.8})$$

Thus, after N intervals, D_n is expressed as:

$$D_n = A \exp(-K J_{\text{eff}} (N t_f)^m) \quad (\text{A.9})$$

where J_{eff} is the equivalent current density and is expressed as:

$$J_{\text{eff}} = \left(\sum_n \frac{(J_n)^{1/m}}{N}\right)^m \quad (\text{A.10})$$

Similarly, since intensity is proportional to current density (i.e., current density can be computed by scaling intensity by the efficiency, luminance, and area of the OLED), normalized luminance intensity I_{eff} in the RGB linear space can also be expressed as:

$$I_{\text{eff}} = \left(\sum_n \frac{(I_n)^{1/m}}{N}\right)^m \quad (\text{A.11})$$

The normalized luminance intensity I_{eff} can be transformed to the equivalent signal level I'_{eff} by using the Formulae (7) and (8) specified in IEC 61966-2-1:1999 as follows:

If $I_{\text{eff}} \leq 0,003\ 130\ 8$

$$I'_{\text{eff}} = 12,92 \times I_{\text{eff}} \quad (\text{A.12})$$

or if $I_{\text{eff}} > 0,003\ 130\ 8$

$$I'_{\text{eff}} = 1,055 \times I_{\text{eff}}^{1,0/2,4} - 0,055 \quad (\text{A.13})$$

where signal level I'_{eff} is the normalized value from 0 to 1.

Another linear to non-linear conversion can also be used for the normalized luminance intensity to the equivalent signal level transformation.

NOTE Some OLED displays control the peak luminance differently by the APL of the input signal. In this case, the luminance intensity I_n for each frame of video could be influenced by its characteristics. The characteristics of the OLED display which control the peak luminance by APL could be measured following the measurement method of luminance loading in [7].

A.2.3 Extraction of the equivalent signal level from the IEC 62087:2011 10-min video loop Examples of extracted equivalent signal level

The Examples of extraction of the maximum and the ~~minimum~~ average equivalent signal levels are demonstrated by using the IEC 62087:2011³ 10-min video loop. If the ~~another video loop~~ is used, then it should be following this method. Assuming the experimental data of $m = 1/1,7$, and the transformation Formula (8) specified in IEC 61966-2-1:1999 for non-linear to linear and linear to non-linear conversion, OLED device primaries are the same as that in IEC 61966-2-1, and take both the RGB and RGBW formats. The maximum and the ~~minimum average~~ equivalent signal levels are summarized in Table A.1. For example, the values are shown in the case where $m = 1/1,7$, gamma is 2,2, ~~the white point is D65~~ and the signal is 8 bits. m is the experimental value, so the maximum and the ~~minimum average~~ equivalent signal levels are recalculated from Formula (A.10) or Formula (A.11) in the case of another m value. They are also re-calculated from Formula (A.12) and Formula (A.13) in case of another gamma value. The images and distribution of signal levels are shown in Figures A.2 and A.3. In the case of an RGB pixel format display, the test input signal to the OLED display panels or modules can be set to generate ~~165, 160, and 163~~ 143, 137, and 142, respectively, as the maximum equivalent signal level over the 4 % window located in the centre of the display and ~~66, 65, and 65~~ 121, 117, and 116, respectively, as the ~~minimum average~~ equivalent signal level over the remaining area simultaneously. However, for the case where the OLED display panels or modules have more than three primaries (i.e. RGBW), the procedure should be separated into multiple procedures with the multiple combination of the equivalent signals as follows:

~~Procedure A: 108,0, 0 as the maximum signal level, 22,0, 0 as the minimum signal level.~~

~~Procedure B: 0,85,0 as the maximum signal level, 0,21,0 as the minimum signal level.~~

~~Procedure C: 0, 0,89, as the maximum signal level, 0, 0,27 as the minimum signal level.~~

~~Procedure D: 151,151,151 as the maximum signal level, 66,66,66 as the minimum signal level.~~

Procedure A: 102, 0, 0 as the maximum signal level, 81, 0, 0 as the average signal level

Procedure B: 0, 77, 0 as the maximum signal level, 0, 65, 0 as the average signal level

Procedure C: 0, 0, 100 as the maximum signal level, 0, 0, 80 as the average signal level

Procedure D: 135, 135, 135 as the maximum signal level, 114, 114, 114 as the average signal level


³ This publication has been withdrawn.

Table A.1 – Examples of the maximum and the ~~minimum~~ average equivalent signal levels (8 bits)

	RGB pixel format		RGBW pixel format	
	Min. signal level	Max. signal level	Min. signal level	Max. signal level
Red	66,0,0	165,0,0	22,0,0	108,0,0
Green	0,65,0	0,160,0	0,21,0	0,85,0
Blue	0,0,65	0,0,163	0,0,27	0,0,89
White	-	-	66,66,66	151,151,151


	RGB pixel format		RGBW pixel format	
	Avg. signal level	Max. signal level	Avg. signal level	Max. signal level
Red	121, 0, 0	143, 0, 0	81, 0, 0	102, 0, 0
Green	0, 117, 0	0, 137, 0	0, 65, 0	0, 77, 0
Blue	0, 0, 116	0, 0, 142	0, 0, 80	0, 0, 100
White	-	-	114, 114, 114	135, 135, 135

IECNORM.COM : Click to view the full PDF of IEC 62341-5-3:2019 RLV

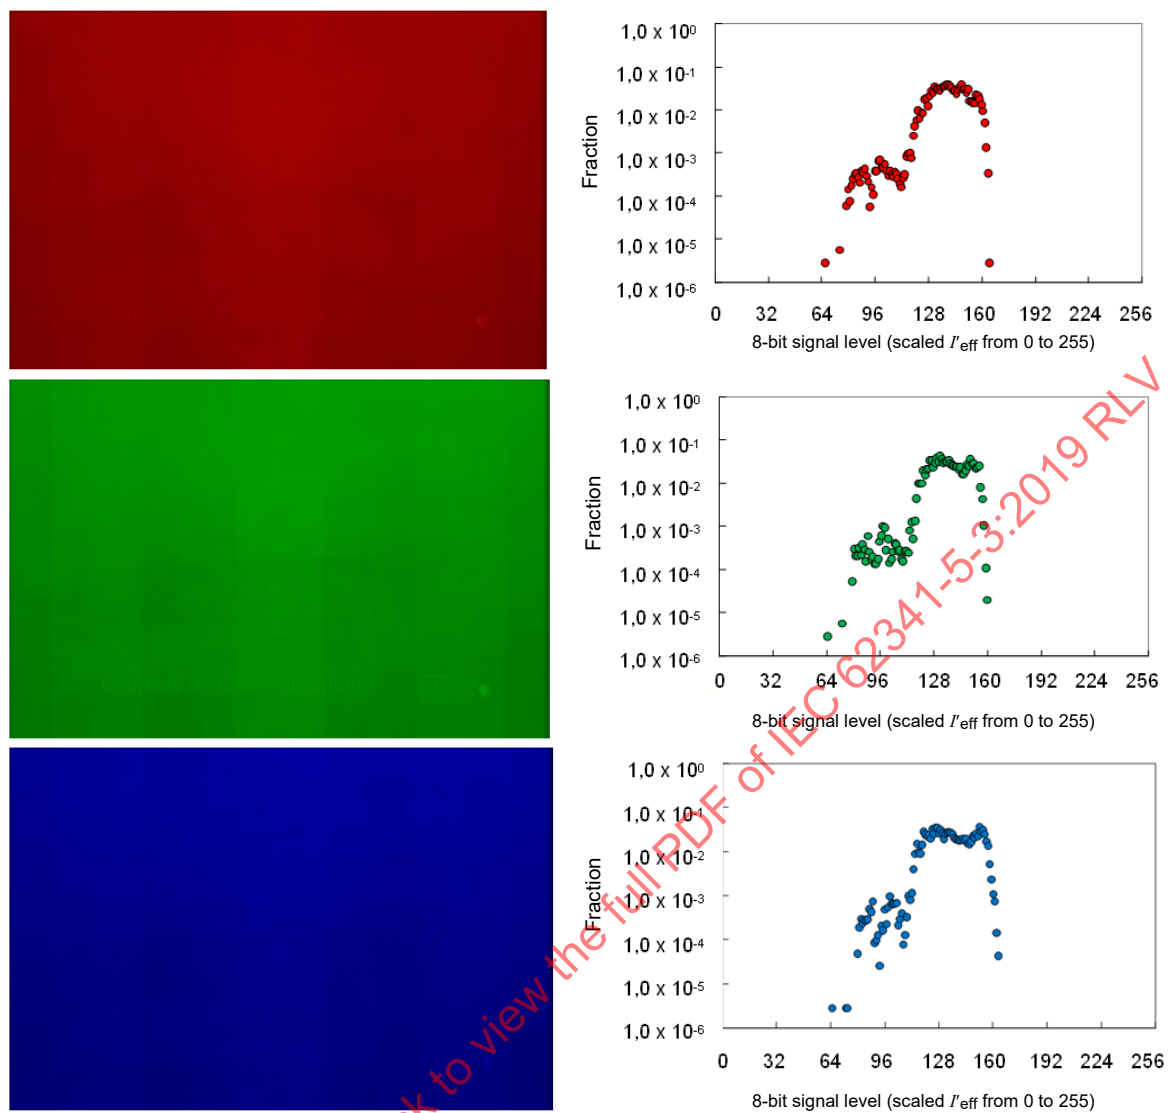


IEC 2161/13

Figure A.2 – Accumulated colour intensity of IEC 62087:2011 10-min video loop in RGB subpixel format with equivalent signal distribution chart based on the left images, respectively

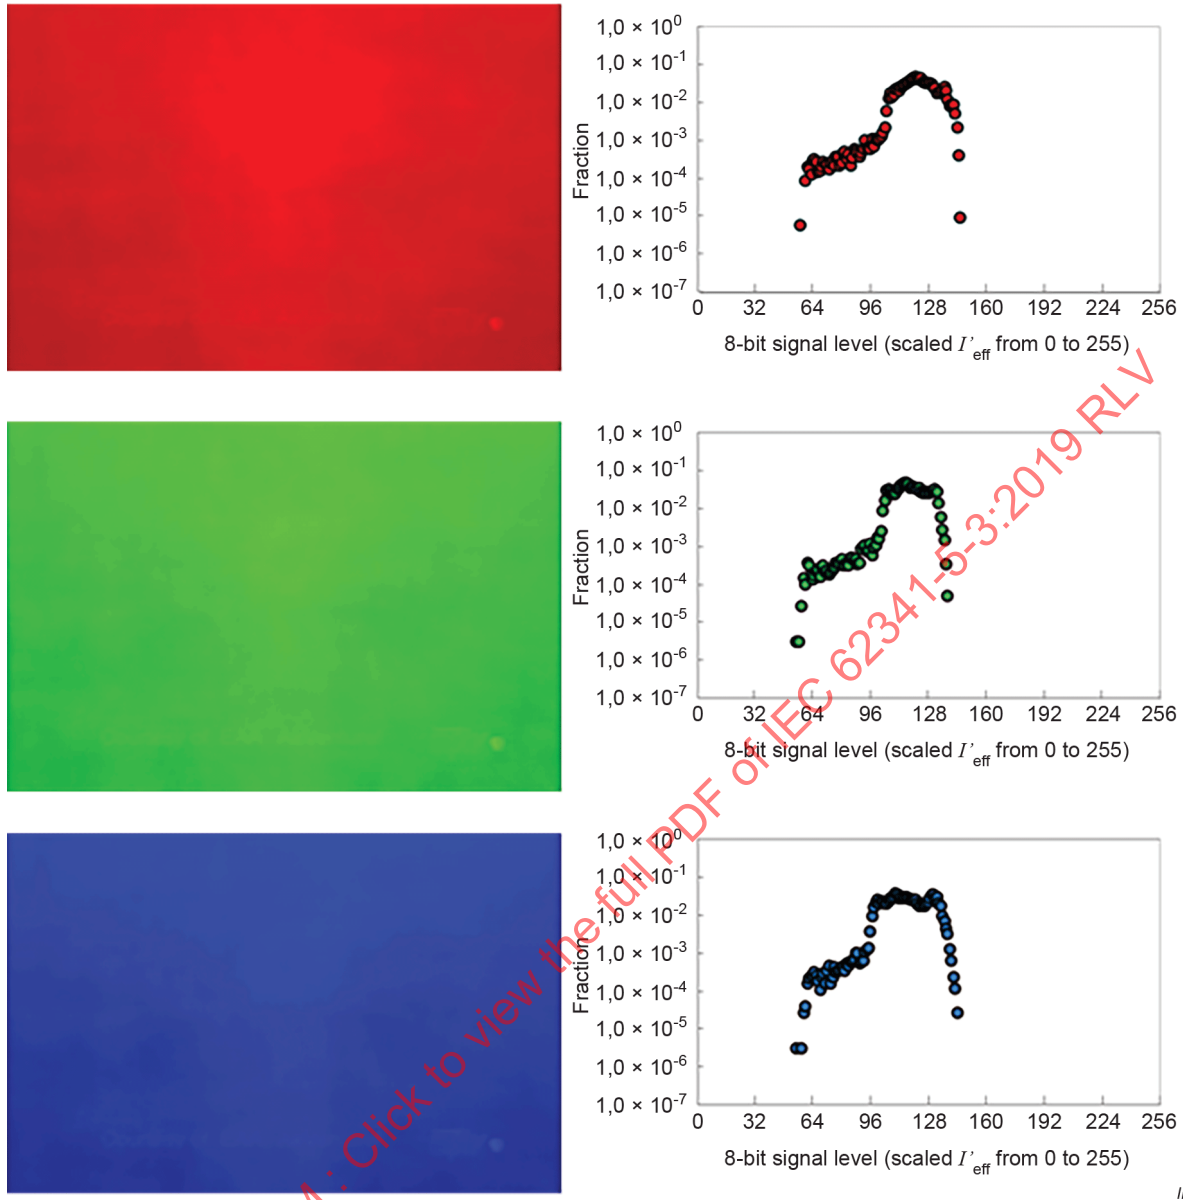


IEC

Figure A.2 – Example of accumulated colour intensity of IEC 62087:2011 10-min video loop in RGB subpixel format with equivalent signal distribution chart based on the left images

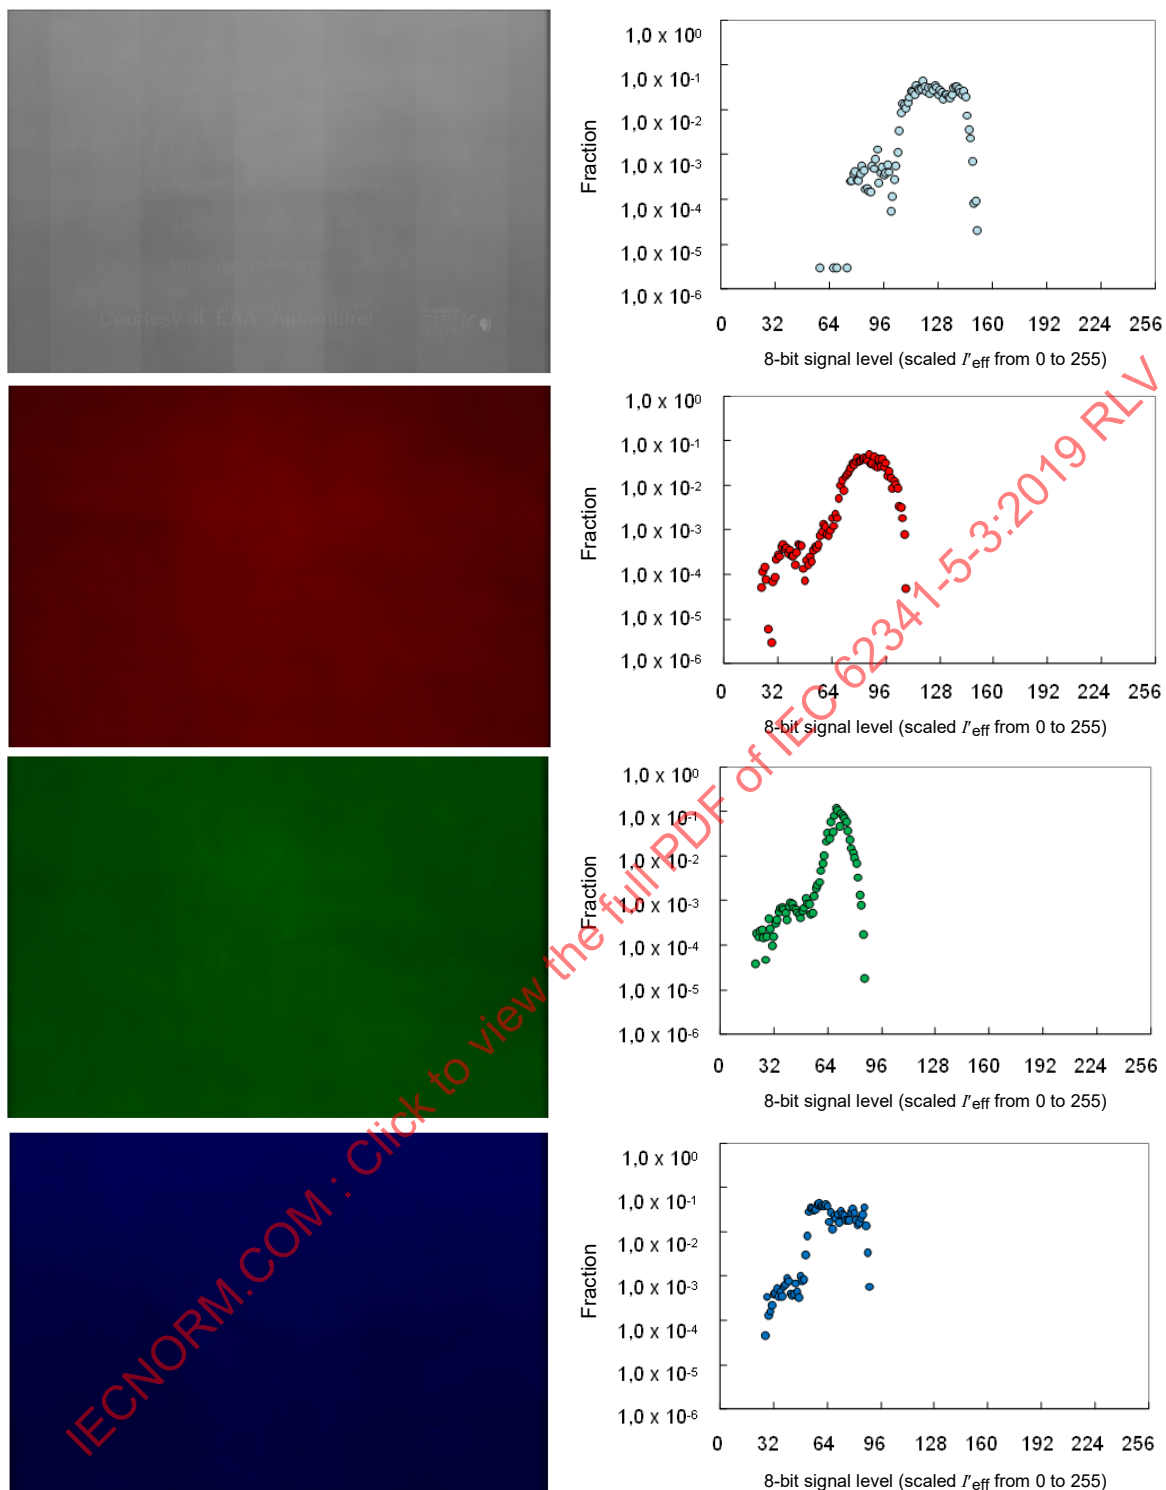

IEC 2162/13

Figure A.3 – Accumulated colour intensity of the IEC 62087:2011 10-min video loop in W, R, G, and B format, with equivalent signal distribution chart based on the left images, respectively

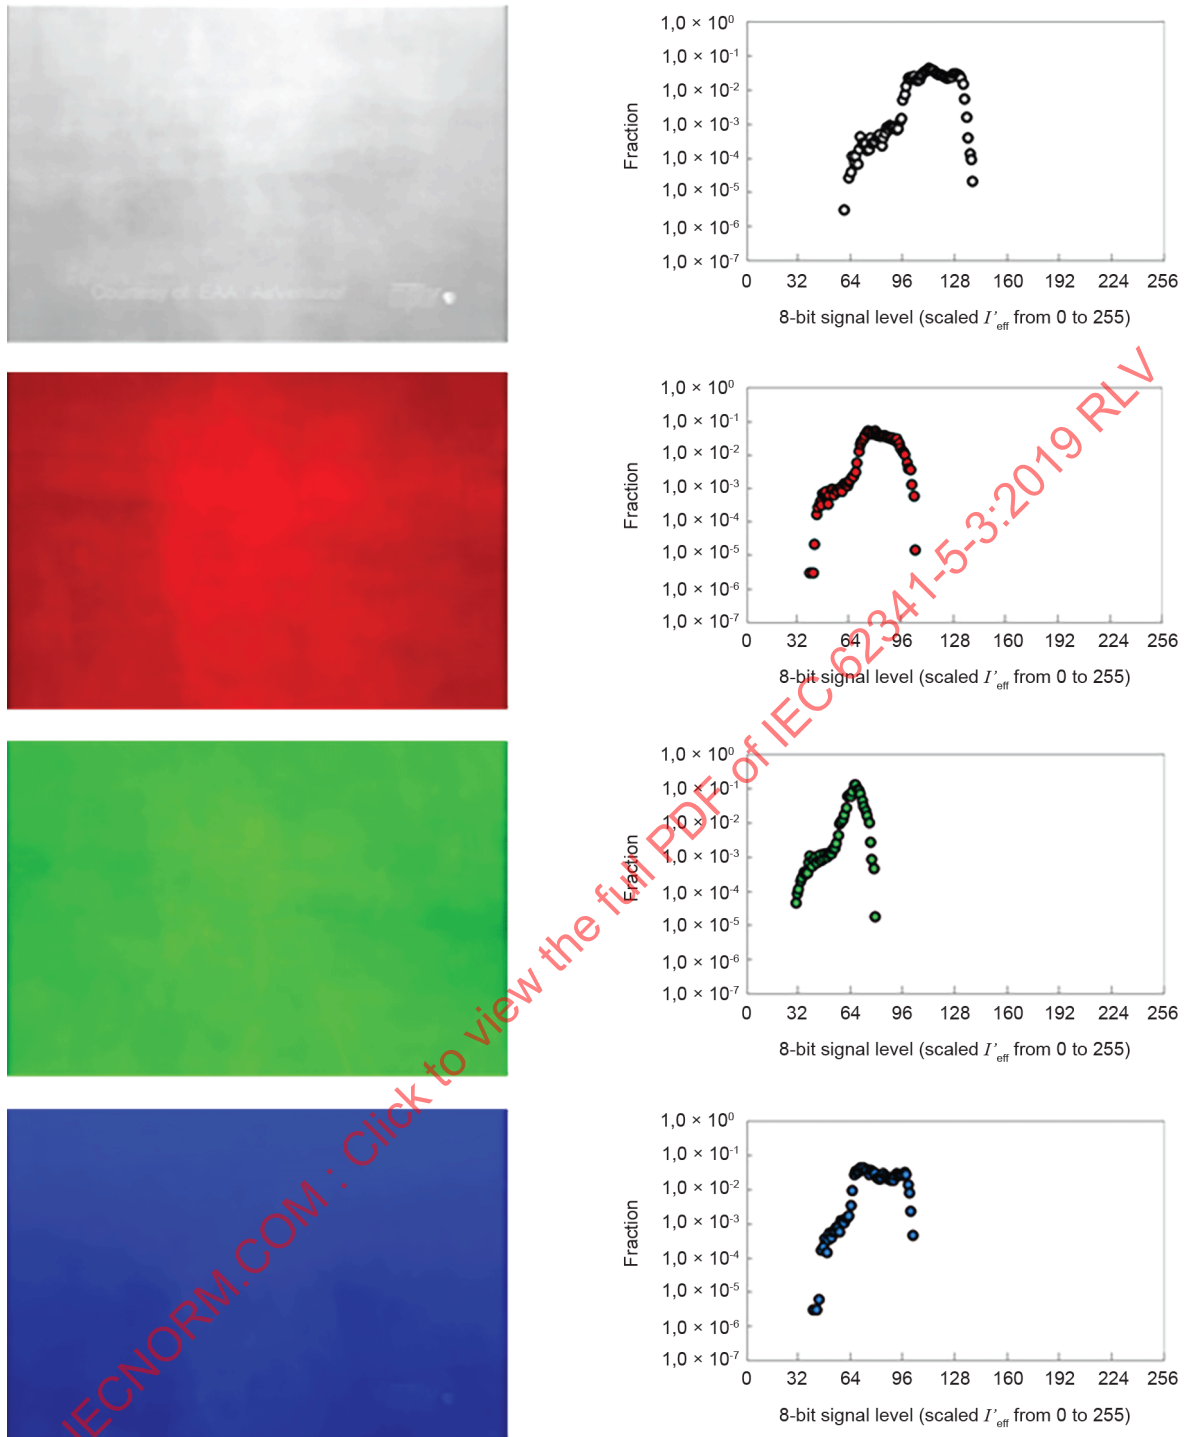

IEC

Figure A.3 – Example of accumulated colour intensity of the IEC 62087:2011 10-min video loop in W, R, G, and B format, with equivalent signal distribution chart based on the left images

Annex B (informative)


Acceleration test of lifetime measurement

B.1 Purpose

The purpose of this method is to reduce the measuring time.

B.2 Acceleration testing

This testing method is carried out in such a way that the luminance degradation shall be enhanced when compared to the standard operation, but the degradation mechanism will be the same. If the degradation mechanism is not changed then the shape of the Weibull distribution will not be changed. Figure B.1 shows examples of the Weibull distribution of the accelerated lifetime test.

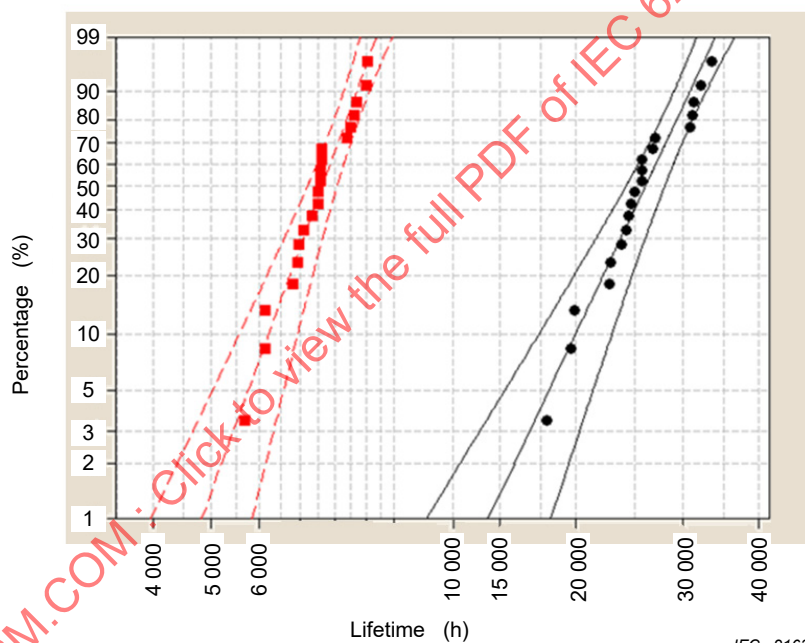

IEC 2163/13

Figure B.1 – Examples of Weibull distributions of accelerated lifetime test

These results can be summarized as shown in Table B.1. The statistical analysis results are shown in Table B.2.

Considering the p value of each hypothesis in this example, it can be seen that although the scale factors are quite different between $Lifetime_1$ and $Lifetime_2$, the shape factors are similar. This means that the acceleration used in this example is valid.

Table B.1 — Summary of the acceleration test results in Figure B.1

		$Lifetime_1$	$Lifetime_2$
Experiments	Luminance level	L_1	L_2
	Marks in Figure A.1	Red square	Black circle
	Number of samples	20	20
Results	Mean (MTTF)	25 674,7	7 525,58
	Std. dev.	4 257,51	976,329
	Scale factor	27 426,6	7,938,0
	Shape factor	7,099 90	9,230 99

Table B.2 — Statistical analysis results of the accelerated lifetime test in Figure B.1

Approval of same shape factor and same scale factor			
χ^2	DF	p	
1 034,82	2	0,000	
Approval of same shape factor			
χ^2	DF	p	
1,249 12	1	0,264	
Approval of same scale factor			
χ^2	DF	p	
865,006	1	0,000	
DF (degrees of freedom): The number of degrees of freedom generally refers to the number of independent observations in a sample minus the number of population parameters that should be estimated from the sample data.			
p -value: A p -value measures the strength of evidence in support of a null hypothesis. Suppose the test statistic in a hypothesis test is equal to S . The p -value is the probability of observing a test statistic as extreme as S , assuming the null hypothesis is true. If the p -value is less than the significance level, the null hypothesis is rejected.			
χ^2 (Chi-square): the chi squared distribution with k degrees of freedom is the distribution of a sum of the squares of k independent standard normal random variables.			

B.3 Acceleration factor

The effect of an acceleration test may be expressed with an acceleration factor. In the examples in Figure B.1, the acceleration parameter is the luminance level. By using Equation (8) the relationship between the different luminance and lifetime is proved. t_1 and t_2 are the different lifetimes, and the luminance levels $L(t_1)$ and $L(t_2)$ are measured by the different lifetimes. Each of the degradation steps is expressed as:

$$Lt_1 = \ln\left(\frac{L(t_1)}{L(0)}\right) = -\left(\frac{t_1}{a}\right)^{1/n} \quad (\text{B.1})$$

$$Lt_2 = \ln\left(\frac{L(t_2)}{L(0)}\right) = -\left(\frac{t_2}{a}\right)^{1/n}$$

Constant a of Equation (B.1) is calculated at t_2 , and the degradation at t_1 is calculated by using t_2 and Lt_2 , which are expressed as:

$$a = -\frac{t_2}{(Lt_2)^n} \quad (\text{B.2})$$

$$Lt_1 = \left\{ \frac{t_1}{t_2 / (Lt_2)^n} \right\}^{1/n} \quad (\text{B.3})$$

In this case the relationship between luminance levels and lifetime may be expressed with Equation (B.4).

$$Lifetime_1 = Lifetime_2 \left(\frac{L_2}{L_1} \right)^n \quad (\text{B.4})$$

where

$Lifetime_i$ is the lifetime operated with a luminance level of L_i ;

L_i is the luminance level of each condition;

n is the acceleration factor.

If the luminance level is used as an acceleration parameter, the typical range of n would be 1,6 ~ 2,0.

Annex B (informative)

Colour difference with CIEDE2000

B.1 Purpose

The purpose of this method is to calculate the colour difference with CIEDE2000 at a target time or at an estimated time with threshold [2], [3].

B.2 Calculation of colour difference

The colour difference formula [3, 4] $\Delta E^*_{00}(t)_0$ caused by image sticking at P_0 over time for white is calculated as follows:

$$\Delta E^*_{00}(t)_0 = \left[\left(\frac{L^*_0(t) - L^*_0(t_0)}{k_L S_L} \right)^2 + \left(\frac{C^*_0(t) - C^*_0(t_0)}{k_C S_C} \right)^2 + \left(\frac{H^*_0(t) - H^*_0(t_0)}{k_H S_H} \right)^2 + R_T \left(\frac{C^*_0(t) - C^*_0(t_0)}{k_C S_C} \right) \left(\frac{H^*_0(t) - H^*_0(t_0)}{k_H S_H} \right) \right]^{\frac{1}{2}} \quad (\text{B.1})$$

where

t is the specified measurement time;

t_0 is the initial measurement time;

L^*_0 is the CIELAB lightness of the measuring locations of P_0 .

C^*_0 is the CIELAB weighted chroma of the measuring locations of P_0 .

H^*_0 is the CIELAB weighted hue of the measuring locations of P_0 .

The average of the colour difference formula $\Delta E^*_{00}(t)_{\text{AVG}}$ caused by image sticking between different measuring locations from P_1 to P_4 for white is calculated as follows:

$$\Delta E^*_{00}(t)_{\text{AVG}} = \left(\sum_{i=1}^4 \left[\left(\frac{L^*_i(t) - L^*_0(t_0)}{k_L S_L} \right)^2 + \left(\frac{C^*_i(t) - C^*_0(t_0)}{k_C S_C} \right)^2 + \left(\frac{H^*_i(t) - H^*_0(t_0)}{k_H S_H} \right)^2 + R_T \left(\frac{C^*_i(t) - C^*_0(t_0)}{k_C S_C} \right) \left(\frac{H^*_i(t) - H^*_0(t_0)}{k_H S_H} \right) \right]^{\frac{1}{2}} \right) / 4 \quad (\text{B.2})$$

where

t is the specified measurement time;

L^*_i is the CIELAB lightness of the measuring locations of P_i .

C^*_i is the CIELAB weighted chroma of the measuring locations of P_i .

H^*_i is the CIELAB weighted hue of the measuring locations of P_i .

Bibliography

- [1] FÉRY, C., B. RACINE, D. VAUFREY, H. DOYEUX, AND S. CINÀ. Physical mechanism responsible for the stretched exponential decay behavior of aging organic light-emitting diodes. *Appl. Phys. Lett.* Nov. 2005, 87, (213502)
- ~~[2] WEIBULL, W. A Statistical Distribution Function of Wide Applicability. *Journal of Applied Mechanics*. 1951, 18, 293-297~~
- [2] Sharma, Gaurav, Wencheng Wu, and Edul N. Dalal. "The CIEDE2000 color-difference formula: Implementation notes, supplementary test data, and mathematical observations." *Color Research & Application* 30.1 (2005): 21-30
- [3] Luo MR, Cui G, Rigg B. The development of the CIE 2000 colour difference formula: CIEDE2000. *Color Res Appl* 2001; 26:340 –350
- [4] KCC, the Korea Broadcast Media Use Environmental Survey 2014 report, (2014)
- [5] Flat Panel Display Measurement Standard, VESA (Video Electronics Standards Association), Display Metrology Committee, Version 2.0, 1 June 2001
- [6] Maekawa Y, Mori N, Kohno M. P-70: Image sticking measuring method by usage model [J]. *SID Symposium Digest of Technical Papers*, 2010, 41(1):1512-1515
- [7] ICDM, Information display measurement standard 1.03
- [8] IEC 62087:2011⁴, *Methods of measurement for the power consumption of audio, video and related equipment*
- [9] IEC 61966-2-1:1999, *Multimedia systems and equipment – Colour measurement and management – Part 2-1: Colour management - Default RGB colour space - sRGB*
IEC 61966-2-1:1999/AMD1:2003

⁴ This publication has been withdrawn and partially replaced by IEC 62087-1:2015, IEC 62087-2:2015, IEC 62087-3:2015, IEC 62087-4:2015, IEC 62087-5:2015, and IEC 62087-6:2015.

IECNORM.COM : Click to view the full PDF of IEC 62341-5-3:2019 RLV

INTERNATIONAL STANDARD



**Organic light emitting diode (OLED) displays –
Part 5-3: Measuring methods of image sticking and lifetime**

IECNORM.COM : Click to view the full PDF of IEC 62341-5-3:2019 RLV

CONTENTS

FOREWORD	4
1 Scope	6
2 Normative references	6
3 Terms, definitions and abbreviated terms	6
3.1 Terms and definitions	6
3.2 Abbreviated terms	7
4 Measuring configuration	7
4.1 General	7
4.2 Light measuring device	8
5 Standard measuring conditions	8
5.1 Standard measuring environmental conditions	8
5.2 Standard measuring darkroom conditions	8
5.3 Standard setup conditions	8
5.3.1 General	8
5.3.2 Adjustment of OLED display	8
5.3.3 Starting conditions of measurements	9
5.3.4 Test patterns	9
5.3.5 Conditions of measuring equipment	11
6 Measuring methods of image sticking	11
6.1 Purpose	11
6.2 Measuring method	11
6.2.1 Measuring equipment	11
6.2.2 Measuring procedure	11
6.3 Analysis and report	12
6.3.1 Analysis	12
6.3.2 Report	14
7 Measuring methods of the luminance lifetime	16
7.1 Purpose	16
7.2 Measuring method	16
7.2.1 Measuring equipment	16
7.2.2 Measuring procedure	16
7.2.3 Estimation of luminance lifetime	17
Annex A (informative) Calculating method for equivalent signal level to reflect the characteristics of the OLED display	19
A.1 Purpose	19
A.2 Determining the equivalent signal level	19
A.2.1 General	19
A.2.2 Calculation of the normalized luminance intensity	19
A.2.3 Examples of extracted equivalent signal level	22
Annex B (informative) Colour difference with CIEDE2000	25
B.1 Purpose	25
B.2 Calculation of colour difference	25
Bibliography	26
Figure 1 – Measuring system and arrangement	7

Figure 2 – Test pattern for SDR displays.....	9
Figure 3 – Image sticking measuring area.....	10
Figure 4 – Test pattern for HDR displays	11
Figure 5 – Example of the resulting image after image stress	12
Figure 6 – Example of luminance behavior in operation for an OLED display module	16
Figure 7 – Example of lifetime estimation with the extrapolation method	17
Figure 8 – Examples of estimated lifetime depending on the time elapsed	18
Figure A.1 – Measured 10 mA/cm ² to 80 mA/cm ² OLED degradation values and corresponding modelled functions with $m = 1 / 1,7$	20
Figure A.2 – Example of accumulated colour intensity of IEC 62087:2011 10-min video loop in RGB subpixel format with equivalent signal distribution chart based on the left images.....	23
Figure A.3 – Example of accumulated colour intensity of the IEC 62087:2011 10-min video loop in W, R, G, and B format, with equivalent signal distribution chart based on the left images	24
Table 1 – Examples of maximum and average code value extracted from video samples	10
Table 2 – Information on test pattern	14
Table 3 – Example of typical value.....	15
Table 4 – Reporting format of the image sticking data at target time	15
Table 5 – Reporting format of the image sticking time with threshold	15
Table A.1 – Examples of the maximum and the average equivalent signal levels (8 bits)	22

INTERNATIONAL ELECTROTECHNICAL COMMISSION

ORGANIC LIGHT EMITTING DIODE (OLED) DISPLAYS –**Part 5-3: Measuring methods of image sticking and lifetime****FOREWORD**

- 1) The International Electrotechnical Commission (IEC) is a worldwide organization for standardization comprising all national electrotechnical committees (IEC National Committees). The object of IEC is to promote international co-operation on all questions concerning standardization in the electrical and electronic fields. To this end and in addition to other activities, IEC publishes International Standards, Technical Specifications, Technical Reports, Publicly Available Specifications (PAS) and Guides (hereafter referred to as “IEC Publication(s)”). Their preparation is entrusted to technical committees; any IEC National Committee interested in the subject dealt with may participate in this preparatory work. International, governmental and non-governmental organizations liaising with the IEC also participate in this preparation. IEC collaborates closely with the International Organization for Standardization (ISO) in accordance with conditions determined by agreement between the two organizations.
- 2) The formal decisions or agreements of IEC on technical matters express, as nearly as possible, an international consensus of opinion on the relevant subjects since each technical committee has representation from all interested IEC National Committees.
- 3) IEC Publications have the form of recommendations for international use and are accepted by IEC National Committees in that sense. While all reasonable efforts are made to ensure that the technical content of IEC Publications is accurate, IEC cannot be held responsible for the way in which they are used or for any misinterpretation by any end user.
- 4) In order to promote international uniformity, IEC National Committees undertake to apply IEC Publications transparently to the maximum extent possible in their national and regional publications. Any divergence between any IEC Publication and the corresponding national or regional publication shall be clearly indicated in the latter.
- 5) IEC itself does not provide any attestation of conformity. Independent certification bodies provide conformity assessment services and, in some areas, access to IEC marks of conformity. IEC is not responsible for any services carried out by independent certification bodies.
- 6) All users should ensure that they have the latest edition of this publication.
- 7) No liability shall attach to IEC or its directors, employees, servants or agents including individual experts and members of its technical committees and IEC National Committees for any personal injury, property damage or other damage of any nature whatsoever, whether direct or indirect, or for costs (including legal fees) and expenses arising out of the publication, use of, or reliance upon, this IEC Publication or any other IEC Publications.
- 8) Attention is drawn to the Normative references cited in this publication. Use of the referenced publications is indispensable for the correct application of this publication.
- 9) Attention is drawn to the possibility that some of the elements of this IEC Publication may be the subject of patent rights. IEC shall not be held responsible for identifying any or all such patent rights.

International Standard IEC 62341-5-3 has been prepared by IEC technical committee 110: Electronic displays.

This second edition replaces the first edition published in 2013. This edition constitutes a technical revision.

This edition includes the following significant technical changes with respect to the previous edition:

- a) the measurement vehicle for lifetime is only for the module;
- b) the measurement method for monitor or TV devices is modified;
- c) the digital signage display is included as an example of OLED devices;
- d) the measurement method with HDR (high dynamic range) for image sticking is added;
- e) the analysis method with CIEDE 2000 is added for image sticking;
- f) the information method for evaluating image sticking is modified.

The text of this standard is based on the following documents:

FDIS	Report on voting
110/1134/FDIS	110/1154/RVD

Full information on the voting for the approval on this standard can be found in the report on voting indicated in the above table.

This publication has been drafted in accordance with the ISO/IEC Directives, Part 2.

A list of all the parts in the IEC 62341 series, under the general title *Organic light emitting diode (OLED) displays*, can be found on the IEC website.

The committee has decided that the contents of this publication will remain unchanged until the stability date indicated on the IEC web site under "<http://webstore.iec.ch>" in the data related to the specific publication. At this date, the publication will be

- reconfirmed;
- withdrawn;
- replaced by a revised edition, or
- amended.

A bilingual version of this publication may be issued at a later date.

IMPORTANT – The 'colour inside' logo on the cover page of this publication indicates that it contains colours which are considered to be useful for the correct understanding of its contents. Users should therefore print this document using a colour printer.

ORGANIC LIGHT EMITTING DIODE (OLED) DISPLAYS –

Part 5-3: Measuring methods of image sticking and lifetime

1 Scope

This part of IEC 62341 specifies the standard measuring methods for determining the image sticking and lifetime of organic light emitting diode (OLED) display panels and modules, except finalized display products for end customers, such as TV sets, monitor sets and mobile phones. The measuring method for the lifetime mainly applies to modules.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60050-845, *International Electrotechnical Vocabulary (IEV) – Part 845: Lighting* (available at <<http://www.electropedia.org>>)

IEC 62341-1-2, *Organic light emitting diode (OLED) displays – Part 1-2: Terminology and letter symbols*

IEC 62341-6-1:2017, *Organic light emitting diode (OLED) displays – Part 6-1: Measuring methods of optical and electro-optical parameters*

ISO 11664-1, *Colorimetry – Part 1: CIE standard colorimetric observers*

CIE 15, *Colorimetry*

3 Terms, definitions and abbreviated terms

3.1 Terms and definitions

For the purposes of this document, the terms and definitions given in IEC 62341-1-2 and IEC 60050-845 and the following apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1.1

equivalent current density

average current density of a certain pixel calculated from a varying luminance per frame image in a moving picture so that luminance degradation becomes similar at the same time

Note 1 to entry: See Annex A.

3.1.2**equivalent signal level**

digital code value from 0 to 255 (in the case of 8 bits) transformed from the normalized luminance of a certain pixel by a specified opto-electronic transfer function (OETF)

Note 1 to entry: See Annex A.

3.2 Abbreviated terms

For the purposes of this document, the following abbreviated terms apply.

APL	average picture level
CIELAB	CIE 1976(L*a*b*) colour space
DUT	devices under test
EOTF	electro-optical transfer function
FWHM	full-width-at-half-maximum
HDR	high dynamic range
LMD	light measuring device
OETF	opto-electronic transfer function
OLED	organic light emitting diode
PQ	perceptual quantizer
SDR	standard dynamic range

4 Measuring configuration**4.1 General**

The system diagrams and/or operating conditions of the measuring equipment shall comply with the structure specified in each item. The measuring system and its arrangement are shown in Figure 1. The details are given in Clause 5.

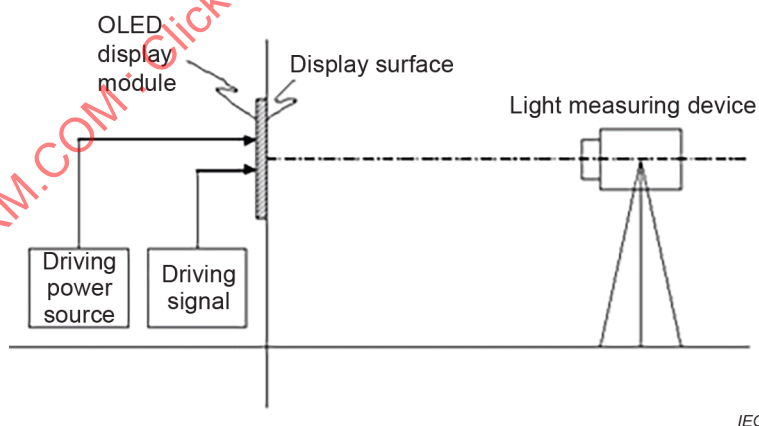


Figure 1 – Measuring system and arrangement

4.2 Light measuring device

The optical properties of displays shall generally be expressed in photometric or colorimetric units using the CIE 1931 standard colorimetric two-degree observer (see ISO 11664-1). Luminance can be measured by a photometer, and the CIE tristimulus values (X , Y , Z) or CIE chromaticity coordinates by a colorimeter. A spectroradiometer can also obtain photometric and colorimetric values through a numerical conversion of the measured spectral radiance data (see, for example, [1]¹). The following requirements are given for these instruments:

The LMD shall be a luminance meter, colorimeter, or a spectroradiometer. For DUTs that have sharp spectral peak full-width-at-half-maximums (FWHMs) smaller than 20 nm, a spectroradiometer should be used. A filter colorimeter should generally not be used for light sources with sharp spectral peaks. If they are used, the colorimeter shall be calibrated with a narrow bandwidth spectroradiometer to give the same results for the specific spectrum. Report the characteristics of the spectroradiometer which is used for calibration. For light sources with sharp spectral peaks, the maximum bandwidth of the spectroradiometer shall be ≤ 5 nm. The higher resolution spectroradiometer produces a more accurate colour measurement. In those cases, the wavelength accuracy shall be within $\pm 0,5$ nm. The spectroradiometer shall be capable of measuring spectral radiance over at least the 380 nm to 780 nm wavelength range, with a maximum bandwidth of 10 nm for smooth broadband spectra (i.e. broad spectrum with no sharp spikes).

Care shall be taken to ensure that the LMD has enough sensitivity and dynamic range to perform the required task. Before measuring the DUT, the LMD specification shall be checked.

5 Standard measuring conditions

5.1 Standard measuring environmental conditions

The standard measuring environmental conditions specified in IEC 62341-6-1:2017, 5.1, shall be applied. For image sticking measurements, the environmental temperature shall be controlled at $25\text{ °C} \pm 3\text{ °C}$, otherwise a temperature-controlled detector shall be used. (The stability of the LMD shall be less than 1/5 of the intended detecting difference levels of luminance and colour.)

5.2 Standard measuring darkroom conditions

The standard measuring darkroom conditions specified in IEC 62341-6-1:2017, 5.2, shall be applied.

5.3 Standard setup conditions

5.3.1 General

Standard setup conditions are given below. Any deviations from these conditions shall be recorded.

5.3.2 Adjustment of OLED display

The adjustment of the OLED display specified in IEC 62341-6-1:2017, 5.3.2, shall be applied.

¹ Numbers in square brackets refer to the Bibliography.

5.3.3 Starting conditions of measurements

Warm-up time is defined as the time elapsed from the moment of switching on the supply voltage until repeated measurements of the display show a variation in luminance of less than 2 %/min. Repeated measurements shall be taken for a period of at least 15 min after starting. The luminance variations shall also not exceed 5 % during the total measurement.

5.3.4 Test patterns

5.3.4.1 SDR displays

The test patterns for SDR display devices such as mobile phones, tablet PCs, monitors, TVs and digital signage are shown in Figure 2. The test pattern for SDR displays is divided into two groups.

1) Test pattern for mobiles and tablet PC displays

In the case of mobiles and tablet PCs, the measurement distance between the display and the LMD depends on the size of the OLED display panels or modules. The measuring distance and the aperture angle may be adjusted to achieve a measuring field greater than 500 pixels if the setting of the measurement field angle is not applied. For display devices except monitors, TVs and digital signage, the test pattern with a white level at the 4 % window box located in the centre and a black level in the background, is used in Figure 2a).

2) Test pattern for monitors, TVs and digital signage displays

For monitors, TVs and digital signage, the test pattern is extracted by video analysis to reflect the characteristics of the video sample. For the test pattern, the maximum code value is allocated at the 4 % window box in the centre and the average code value is in the background. The examples of the maximum and average gray code values are shown in Table 1. The example of the test pattern is shown in Figure 2b). The maximum and average code values between 0 and 255 (in the case of 8 bits) could be extracted from the accumulating image for all frames of the video sample, which is converted as equivalent grayscale from each colour channel.

NOTE 1 Image sticking is influenced by the characteristics of the OLED displays [5], [7]. Some manufacturers of OLED displays apply various algorithms to optimize the quality of each device, and this also influences the image sticking. To consider the characteristics of an OLED display, the method in Annex A is used for the test pattern reflecting the characteristics of the OLED display.

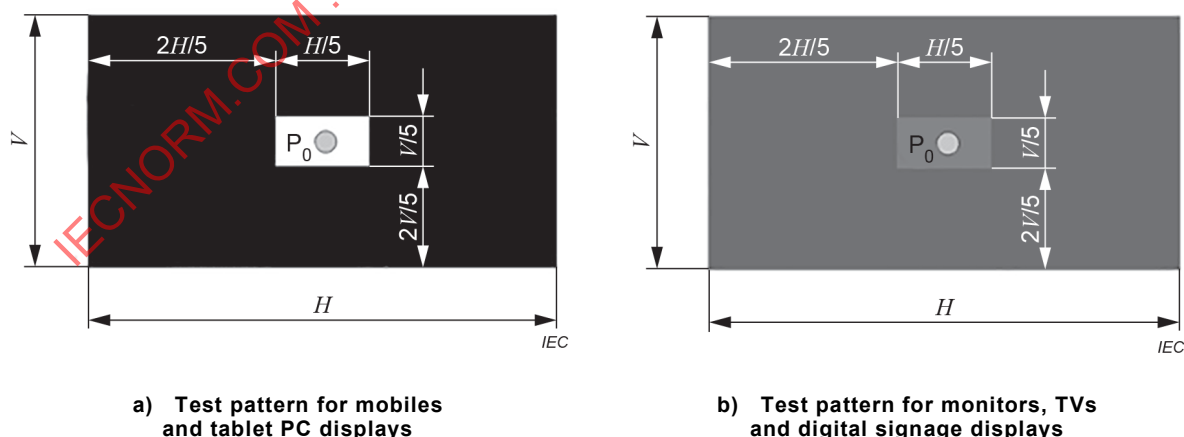


Figure 2 – Test pattern for SDR displays

Table 1 – Examples of maximum and average code value extracted from video samples

Examples of test video	Maximum code value	Average code value
IEC 62087:2011	107	84
Broadcast video sample	183	102

NOTE 2 For the test pattern, any video samples could be selected as needed. Table 1 shows two kinds of representative examples. The broadcast video sample example is constructed by considering the viewing ratio of the content of TV programmes based on the Korea broadcast media use environmental survey report: entertainment (30,9%), news (20,2 %), drama (16,8 %), and so on [4]. The average gray level and test pattern size are different between SDR and HDR in TVs. Depending on the purpose of the test, Figure 2b) or Figure 4a) would apply.

3) Measuring area

In order to get repeatability of measurement, the measuring area from P_0 to P_4 for displays is set to consider the uniformity of the OLED display panels or modules, as shown in Figure 3. If the centre window size is changed, then it should be reported in Table 2.

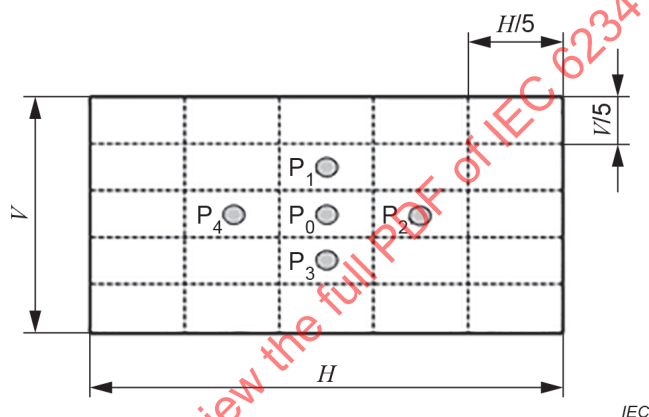


Figure 3 – Image sticking measuring area

4) Checking the test pattern

For SDR displays, the output luminance can be different although they have the same digital code value inputs. To check the brief information of the selected test pattern, the output luminance for the test pattern should be measured and reported.

Apply the test pattern on OLED displays and measure the output luminance on the measuring area from P_0 to P_4 as shown in Figure 3. The results of the output luminance of the test pattern should be reported in Table 2.

5.3.4.2 HDR displays

In 5.3.4.1, the test pattern for SDR displays is described. The test pattern for HDR displays is shown in Figure 4a). It is based on the PQ curve and 10 bits. The test pattern for HDR displays is proposed separately because the characteristics of the contents of the SDR and HDR are different. The test pattern for SDR or HDR can be used as needed. The background code value should be 510. The size of the box window should be 10 %, which is located in the centre. The code value of the 10 % box window should be 710. The measured luminance of the box window and the background luminance should be reported. To get repeatability of the measurement data, the measuring area from P_0 to P_4 is the centre of the boxes, as shown in Figure 4b). The measurement data should be reported in Table 2.

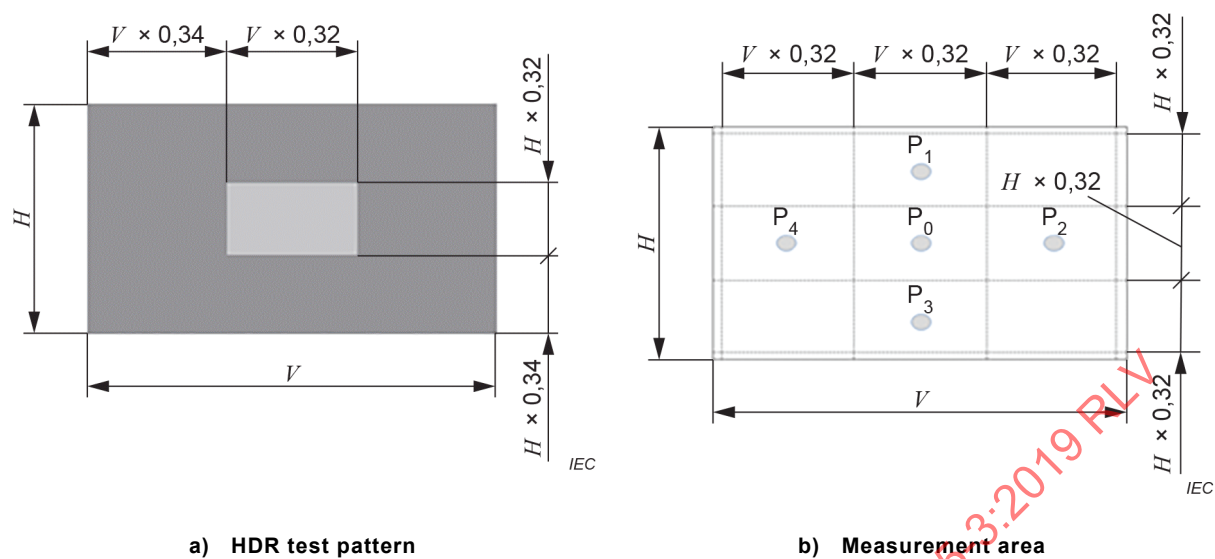


Figure 4 – Test pattern for HDR displays

NOTE The code value of the 10 % box window and background is the result of the analysed data of HDR contents which are HDR games, drama and documentary.

5.3.5 Conditions of measuring equipment

The general conditions in IEC 62341-6-1:2017, Clause 5, shall be applied.

6 Measuring methods of image sticking

6.1 Purpose

The purpose of this method is to measure the image sticking of an OLED display.

6.2 Measuring method

6.2.1 Measuring equipment

The following equipment defined in IEC 62341-6-1:2017, 5.3.4, shall be used:

- a) power supplies and signal sources for driving,
- b) LMD.

6.2.2 Measuring procedure

The OLED display shall be set in darkroom conditions for measurement.

a) Initial measurements on full screen pattern

Apply a full white screen driving signal to the OLED display, and set all power supplies to the standard operation conditions.

Measure the initial spectral radiance or tristimulus values at P_0 to P_4 as shown in Figure 3. The initial spectra radiance or tristimulus values of the primary colours may also be measured individually.

b) Image stress using the test pattern

For image stress, the test pattern based on 5.3.4 for display devices should be applied to the OLED display.

Keep the test pattern until the specified time, considering the luminance degradation curve. For example, the measurement time can be every 1 h during the first 6 h, and every 24 h during the first 120 h, then every 72 h until the target time in the standard measurement condition. Alternatively keep the test pattern until the target time in the standard measurement condition.

c) Measurements on full screen pattern after image stress

Before the measurement, turn off the OLED display and stabilize it to the standard operation condition. Then turn on the OLED display again and apply a full white screen driving signal to the OLED display over the full screen. Set all power supplies also to the standard operation conditions. Measure the spectral radiance or the tristimulus values at the same measuring location as the initial measurement. The initial and final spectra radiance or tristimulus values of the individual primary colours may also be measured and reported.

For the measurement method, only white tone is considered. For the other primary colours such as red, green and blue, each test pattern should be designed following the methods of 5.3.4, and each full primary colour screen pattern should be used for measurement.

All measurements shall be done at the target time of 500 h and shall be reported. In Figure 5, an example of image stress is shown.

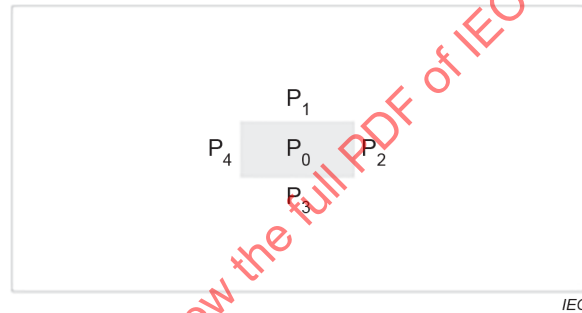


Figure 5 – Example of the resulting image after image stress

6.3 Analysis and report

6.3.1 Analysis

6.3.1.1 Luminance and chromatic deviation method

Image sticking can be characterized by luminance and chromatic deviation.

The image sticking of luminance $IS(t)$ for white is calculated as follows:

$$IS(t) = \left| 1 - \frac{\sum_{i=1}^4 L_i(t) / L_0(t)}{\sum_{i=1}^4 L_i(t_0) / L_0(t_0)} \right| \times 100 \text{ (%) } \quad (1)$$

where

t is the specified measurement time;

t_0 is the initial measurement time;

L_i is the luminance of the measurement location from P_i .

Chromatic deviation $\Delta u'v'(t)_0$ caused by image sticking at P_0 over time for white is calculated as follows:

$$\Delta u'v'(t)_0 = \sqrt{\{u'(t) - u'(t_0)\}^2 + \{v'(t) - v'(t_0)\}^2} \quad (2)$$

where

- t is the specified measurement time;
 t_0 is the initial measurement time;
 $(u'(t), v'(t))$ is the white chromaticity value at the specified time;
 $(u'(t_0), v'(t_0))$ is the white chromaticity value at the initial time.

The average of the chromatic deviation $\Delta u'v'(t)_{AVG}$ caused by image sticking between different measuring locations from P_1 to P_4 for white is calculated as follows:

$$\Delta u'v'(t)_{AVG} = (\sum_{i=1}^4 \sqrt{\{u'_i(t) - u'_0(t)\}^2 + \{v'_i(t) - v'_0(t)\}^2}) / 4 \quad (3)$$

where

- t is the specified measurement time;
 $(u'_i(t), v'_i(t))$ are the chromaticity coordinates of the measuring locations of P_i ($i = 1, 2, 3, 4$).

The value of u' and v' can be calculated from the tristimulus value X , Y , and Z using the following formula:

$$\begin{aligned} u' &= 4X / (X + 15Y + 3Z) \\ v' &= 9Y / (X + 15Y + 3Z) \end{aligned} \quad (4)$$

6.3.1.2 Colour difference method

6.3.1.2.1 General

The image sticking shall be analyzed with ΔE^*_{ab} of the three-dimensional, CIE 1976 $L^*a^*b^*$ colour space (see CIE 15) following the procedure in 6.2.2. Additional three-dimensional uniform colour spaces may also be used and identified in the test report. Each colour point can be plotted on the L^* , a^* , and b^* axes of the CIE $L^*a^*b^*$ colour space by referencing the peak white tristimulus value (X_n , Y_n , Z_n) in the measuring location P_0 at the initial time t_0 and using the following transformation formula:

$$\begin{aligned} L^*_i(t) &= 116 \times f(Y_i(t) / Y_n) - 16 \\ a^*_i(t) &= 500 \times [f(X_i(t) / X_n) - f(Y_i(t) / Y_n)] \\ b^*_i(t) &= 200 \times [f(Y_i(t) / Y_n) - f(Z_i(t) / Z_n)] \end{aligned} \quad (5)$$

where

$$f(x) = \begin{cases} x^{1/3} & x > (6/29)^3 \\ \frac{1}{3} \left(\frac{29}{6}\right)^2 x + \frac{4}{29} & \text{otherwise} \end{cases}$$

- t is the specified measurement time;
 L^*_i, a^*_i, b^*_i is the CIELAB colour coordinates of the measuring locations of P_i ($i = 0, 1, 2, 3, 4$);
 (X_n, Y_n, Z_n) is the tristimulus value of the reference white in the measuring location P_0 at the initial time t_0 .

6.3.1.2.2 CIE 1976

The colour difference formula $\Delta E^*_{ab}(t)_0$ caused by image sticking at P_0 over time for white is calculated as follows:

$$\Delta E^*_{ab}(t)_0 = \sqrt{\{L^*_0(t) - L^*_0(t_0)\}^2 + \{a^*_0(t) - a^*_0(t_0)\}^2 + \{b^*_0(t) - b^*_0(t_0)\}^2} \quad (6)$$

where

t is the specified measurement time;

t_0 is the initial measurement time;

$L^*_0 a^*_0 b^*_0$ are the CIELAB colour coordinates of the measuring locations of P_0 .

The average of the colour difference formula $\Delta E^*_{ab}(t)_{AVG}$ caused by image sticking between different measuring locations from P_1 to P_4 for white is calculated as follows:

$$\Delta E^*_{ab}(t)_{AVG} = \left(\sum_{i=1}^4 \sqrt{\{L^*_i(t) - L^*_0(t_0)\}^2 + \{a^*_i(t) - a^*_0(t_0)\}^2 + \{b^*_i(t) - b^*_0(t_0)\}^2} \right) / 4 \quad (7)$$

where

t is the specified measurement time;

$L^*_i a^*_i b^*_i$ are the chromaticity coordinates of the measuring locations of P_i ($i = 1, 2, 3, 4$).

6.3.2 Report

6.3.2.1 Information of test pattern

Before reporting the measurement data, information on the used test pattern should be reported, as shown in Table 2. It includes the type of test pattern, the size of the window box, the allocated code values located at the centre and background, and the output luminance of OLED displays for the test pattern. If other test patterns not listed in 5.3.4 are used, they should be reported in accordance with Table 2.

Table 2 – Information on test pattern

Types of test pattern		(SDR, HDR, etc.)
Size of window box		- %
Code value	Centre	– (based on 8 or 10 bits)
	Background	– (based on 8 or 10 bits)
Output luminance	Centre	(P_0)
	Background	(average of from P_1 to P_4)

6.3.2.2 Measurement data record

The typical value of image sticking can be reported following the format shown in Table 3. For the typical value, the initial data should be reported and other data at the specified time can be selected following the measuring procedure of image stress.