

INTERNATIONAL STANDARD



375

INTERNATIONAL ORGANIZATION FOR STANDARDIZATION • МЕЖДУНАРОДНАЯ ОРГАНИЗАЦИЯ ПО СТАНДАРТИЗАЦИИ • ORGANISATION INTERNATIONALE DE NORMALISATION

Steel — Tensile testing of tubes

Acier — Essai de traction des tubes

First edition — 1974-08-01

STANDARDSISO.COM : Click to view the full PDF of ISO 375:1974

To become
ISO 6892-1984

UDC 669.14 : 621-462 : 620.172

Ref. No. ISO 375-1974 (E)

Descriptors : steels, steel products, tubes, steel tubes, tests, mechanical tests, tension tests, elongation, elongation after fracture, permanent elongation, elastic limit.

Price based on 13 pages

FOREWORD

ISO (the International Organization for Standardization) is a worldwide federation of national standards institutes (ISO Member Bodies). The work of developing International Standards is carried out through ISO Technical Committees. Every Member Body interested in a subject for which a Technical Committee has been set up has the right to be represented on that Committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work.

Draft International Standards adopted by the Technical Committees are circulated to the Member Bodies for approval before their acceptance as International Standards by the ISO Council.

International Standard ISO 375 was drawn up by Technical Committee ISO/TC 17, *Steel*, and circulated to the Member Bodies in March 1972.

It has been approved by the Member Bodies of the following countries :

Australia	France	Romania
Austria	Germany	South Africa, Rep. of
Belgium	Hungary	Spain
Canada	India	Sweden
Chile	Ireland	Switzerland
Czechoslovakia	Italy	Thailand
Denmark	Netherlands	Turkey
Egypt, Arab Rep. of	New Zealand	United Kingdom
Finland	Poland	U.S.A.

The Member Bodies of the following countries expressed disapproval of the document on technical grounds :

Japan
Norway

This International Standard cancels and replaces ISO Recommendation R 375-1964.

Steel – Tensile testing of tubes

1 SCOPE AND FIELD OF APPLICATION

This International Standard specifies requirements for the tensile testing of complete steel tubes or longitudinal strips of full thickness cut from steel tubes having a cross-sectional area generally not less than 40 mm² (0.06 in²). The longitudinal strip test is not, however, usually carried out on tubes less than 0,5 mm (0.02 in) thick.

Test pieces which are machined all over are to be of the form described in ISO 82 and are to be tested in accordance with its requirements.

NOTE – Test pieces, consisting of strips cut transversely from tubes, are to be prepared and treated in accordance with the material specification and then tested in accordance with the requirements of ISO 82 or ISO 86 according to whether the thickness is equal to or greater than 3 mm (0.12 in), or less than this value.

For welded tubes, the position of the weld in relation to the test pieces is to be in accordance with the material specification.

For the tensile testing of other steel products, ISO 82, ISO 86 and ISO 89 are applicable.

2 REFERENCES

ISO 82, *Steel – Tensile testing*.

ISO 86, *Steel – Tensile testing of sheet and strip less than 3 mm and not less than 0,5 mm thick*.

ISO 89, *Steel – Tensile testing of wire*.

ISO/R 147, *Load calibration of testing machines for tensile testing of steel*.

ISO/R 205, *Determination of proof stress and proving test for steel at elevated temperatures*.

ISO/R 336, *Plain end steel tubes, welded or seamless – General table of dimensions and masses per unit length*.

ISO/R 783, *Mechanical testing of steel at elevated temperatures – Determination of lower yield stress and proof stress and proving test*.

ISO 2566/1, *Steel – Conversion of elongation values – Part 1 : Carbon and low alloy steels*.

ISO 2573, *Determination of K-values of a tensile testing system*.¹⁾

3 PRINCIPLE

The test consists in straining a test piece by tensile stress, generally to fracture, with a view to determining one or more of the mechanical properties enumerated hereafter.

The test is carried out at ambient temperature unless otherwise specified. For tests at elevated temperatures, ISO/R 205 and ISO/R 783 are applicable.

1) At present at the stage of draft.

4 DEFINITIONS

4.1 gauge length : The prescribed part of the cylindrical or prismatic portion of the test piece on which elongation is measured at any moment during the test. In particular, a distinction is to be made between the following :

4.1.1 original gauge length (L_o) : Gauge length before the test piece is strained;

4.1.2 final gauge length (L_u) : Gauge length after the test piece has been fractured and the fractured parts have been carefully fitted together so that they lie in a straight line.

4.2 extensometer gauge length (L_e) : The length of the parallel portion of the test piece used for the measurement of extension by means of an extensometer. (The length may differ from L_o and may be any value greater than b (see clause 5) but less than the parallel length L_c .)

4.3 percentage permanent elongation : Increase in the gauge length of a test piece subjected to a prescribed stress (see 4.1.2) and after removal of the stress, expressed as a percentage of the original gauge length. If a symbol for this elongation is used it is to be supplemented by an index indicating the prescribed stress.

4.4 percentage elongation after fracture (A) : Permanent elongation of the gauge length after fracture, $L_u - L_o$, expressed as a percentage of the original gauge length, L_o .

NOTE — If the gauge length is other than $5,65 \sqrt{S_o}$, where S_o is the original cross-sectional area, A is to be supplemented by a suffix indicating the gauge length used, for example :

A_{10} = percentage elongation on gauge length of $10 \sqrt{4 S_o / \pi}$.

4.5 percentage reduction of area (Z) : Ratio of the maximum change in cross-sectional area which has occurred during the test, $S_o - S_u$, to the original cross-sectional area, S_o , expressed as a percentage. (S_u = minimum cross-sectional area after fracture.) (See also clause 19.)

4.6 maximum load (F_m) : The highest load which the test piece withstands during the test.

4.7 stress (actually "nominal stress") : At any moment during the test, load divided by the original cross-sectional area of the test piece.

4.8 tensile strength (R_m) : Maximum load divided by the original cross-sectional area of the test piece, i.e. stress corresponding to the maximum load.

4.9 yield stresses : In a steel which exhibits a yield phenomenon, a point is reached during the test at which plastic deformation, soon after it has been initiated, continues to occur at nearly constant stress.

4.9.1 upper yield stress (R_{eH}) : The value of stress measured at the commencement of plastic deformation at yield (see figure 3);

or

the value of stress measured at the first peak, obtained during yielding even when that peak is equal to or less than any subsequent peaks observed during plastic deformation at yield (see figure 4).

4.9.2 lower yield stress (R_{eL}) : The lowest value of stress measured during plastic deformation at yield, ignoring any initial transient effects which might occur. (See figures 3 and 4.)

NOTE — If a steel which usually exhibits a yield phenomenon is in a cold-worked or heat-treated condition, the yield phenomenon may not exist. In such cases a proof stress must be specified. (See 4.10 and 4.11.)

4.10 proof stress (non-proportional elongation) (R_p) : The stress at which a non-proportional elongation, equal to a specified percentage of the original gauge length, occurs. (See figure 7.)

When a proof stress (R_p) is specified, the non-proportional elongation is to be stated (for example 0,2 %) and the symbol used for the stress is to be supplemented by an index giving this prescribed percentage of the original gauge length, $R_{p0,2}$.

4.11 proof stress (total elongation) or proof stress under load (R_t) : The stress at which a non-proportional elongation plus elastic elongation, equal to a specified percentage of the original gauge length, occurs. (See figure 8.)

When a proof stress (R_t) is specified, or agreed between the interested parties, the total elongation is to be stated and the symbol used for the stress is to be supplemented by an appropriate index, for example $R_{t0,5}$. (See also 15.3.2.)

NOTE — The value obtained by this total elongation method will only be equivalent to R_p if suitable allowance is made for the measurement of elastic extension.

4.12 permanent set stress (R_r); (stress at permanent set limit) : The stress at which, after removal of load, a prescribed permanent elongation, expressed as a percentage of the original gauge length, occurs. The symbol used for this stress is to be supplemented by an index giving the prescribed percentage of the original gauge length, for example $R_{r0,2}$. (See figure 9.)

5 SYMBOLS AND DESIGNATIONS

Symbols and designations are given in the table below.

Number	Preferred symbol	Designation
1	D	External diameter of round tube, or, with tubes of other sections, diameter of the minimum circumscribing circle ¹⁾
2	a	Thickness of tube (Figures 1 and 2)
3	b	Mean width of longitudinal strip (Figure 2)
4	L_o ²⁾	Original gauge length (Figures 1 and 2)
5	L_c	Parallel length (Figure 2)
—	L_e	Extensometer gauge length
6	L_t	Total length (Figures 1 and 2)
7	—	Gripped ends (Figures 1 and 2)
8	L_u	Final gauge length after fracture (Figures 1 and 2)
9	$L_u - L_o$	Permanent elongation after fracture (Figure 10)
10	A	Percentage elongation after fracture $\left(\frac{L_u - L_o}{L_o} \right) 100$
11	S_o	Original cross-sectional area of the gauge length (Figure 1)
12	S_u	Minimum cross-sectional area after fracture (Figures 1 and 2)
13	R_{eH}	Upper yield stress or upper yield point ³⁾ (Figures 3, 4 and 5)
14	R_{eL}	Lower yield stress or lower yield point ³⁾ (Figures 3, 4 and 5)
15	R_p (e.g. $R_{p0,2}$)	Proof stress (non-proportional elongation) or yield strength (offset) ³⁾ (Figure 7) (0,2 % non-proportional elongation)
16	R_t (e.g. $R_{t0,5}$)	Proof stress (total elongation) or yield strength (total elongation) ³⁾ (Figure 8) (0,5 % total elongation)
17	R_r (e.g. $R_{r0,2}$)	Permanent set stress (Figure 9) (0,2 % permanent set stress)
18	F_m	Maximum load
19	Z	Percentage reduction of area $\left(\frac{S_o - S_u}{S_o} \right) 100$
20	R_m ²⁾	Tensile strength $\frac{F_m}{S_o}$ (Figure 10)

1) The minimum circumscribing circle is the smallest circle which completely circumscribes the whole periphery of the cross-section, but it need not pass through more than two points.

2) In correspondence and where no misunderstanding is possible, the symbols L_o and R_m may be replaced by L and R respectively.

3) The latter term is used in the U.S.A. and in Canada.

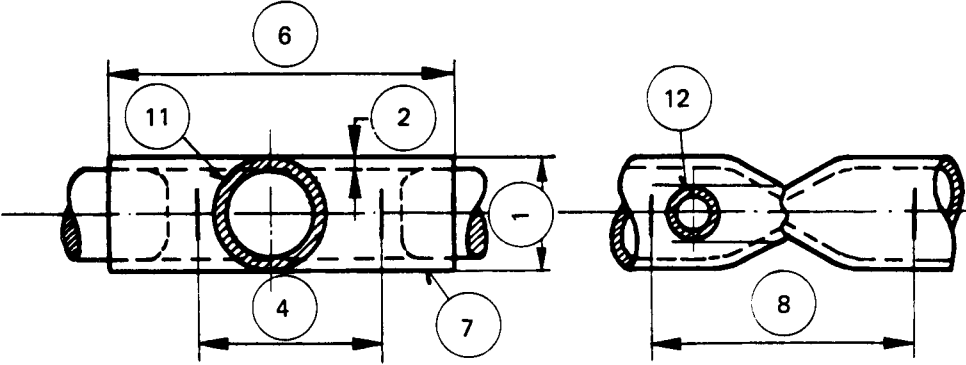


FIGURE 1 – Test on full section

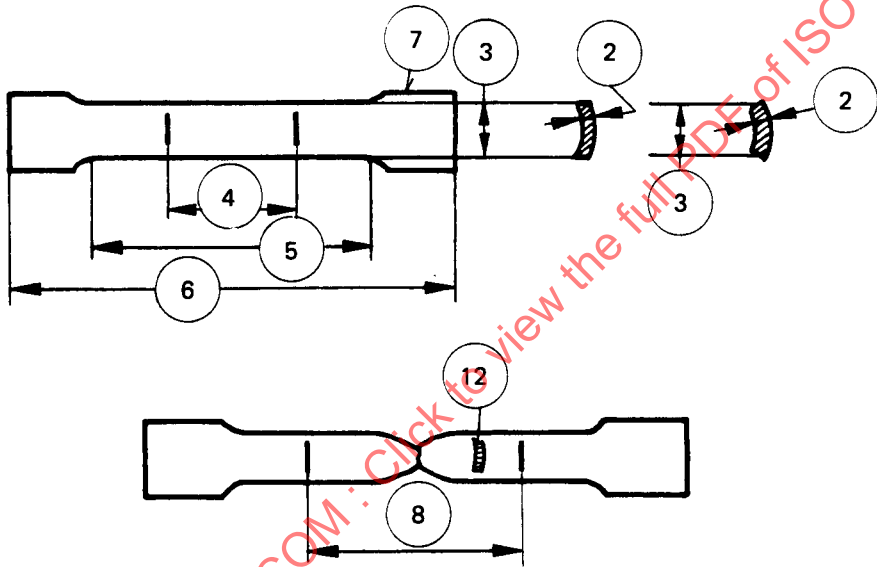


FIGURE 2 – Test on longitudinal strip

Load/extension diagrams illustrating yield :

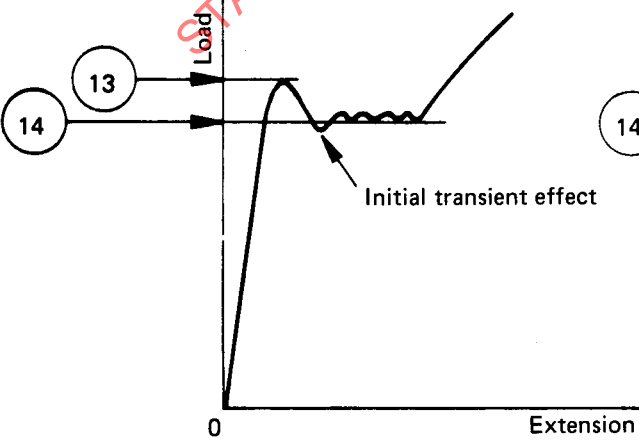


FIGURE 3

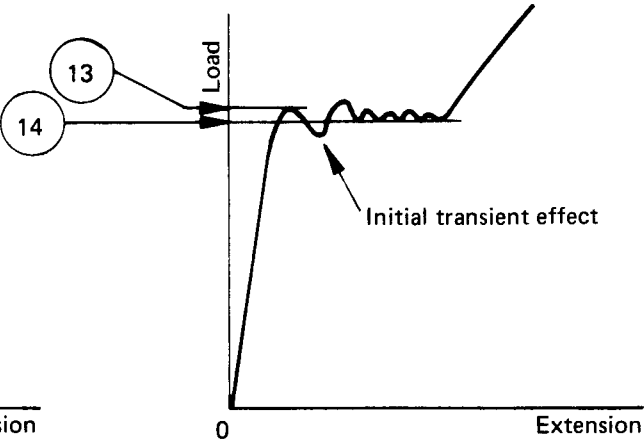


FIGURE 4

Load/extension diagrams :

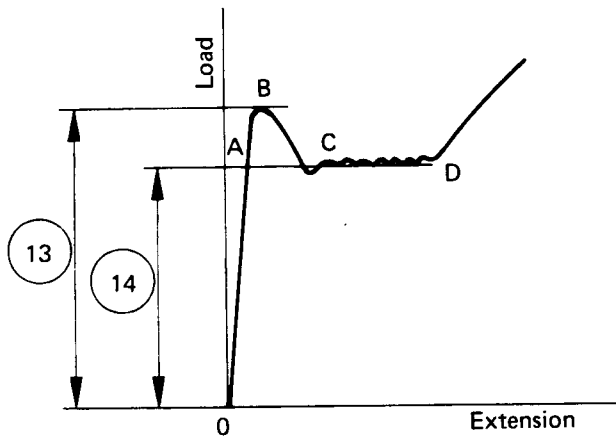


FIGURE 5

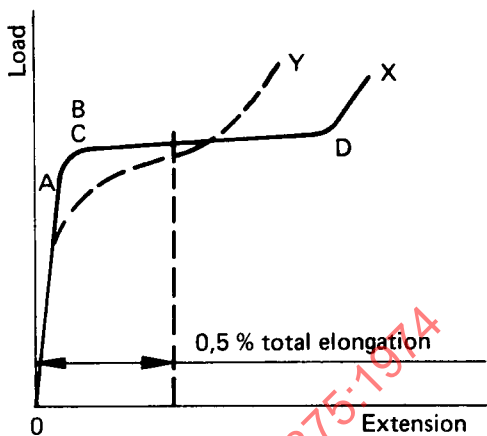


FIGURE 6

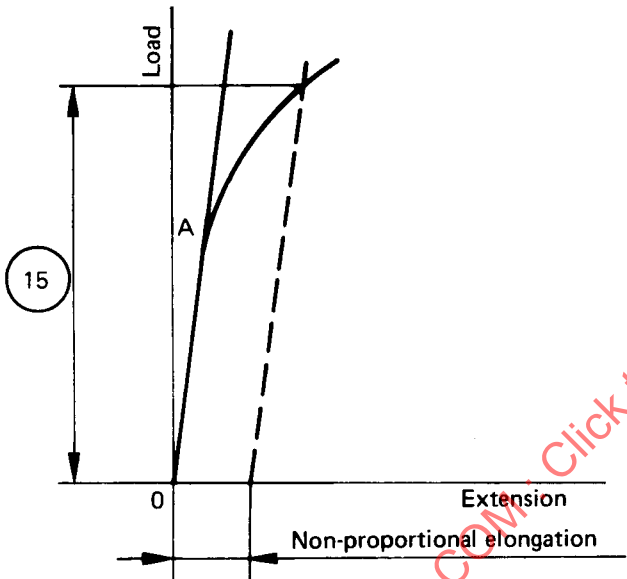


FIGURE 7

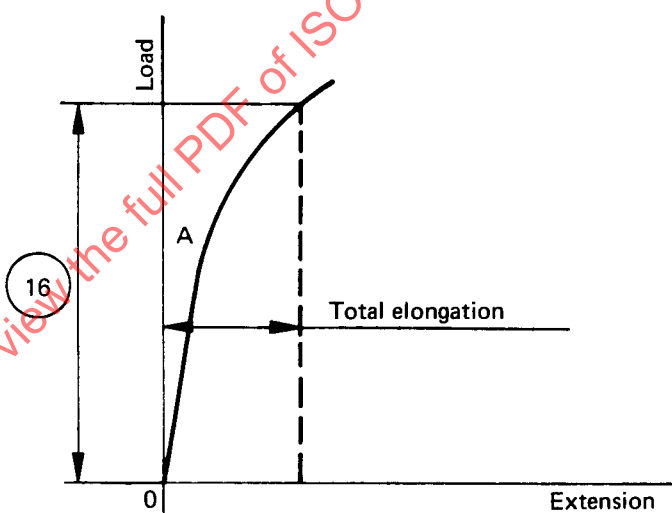


FIGURE 8

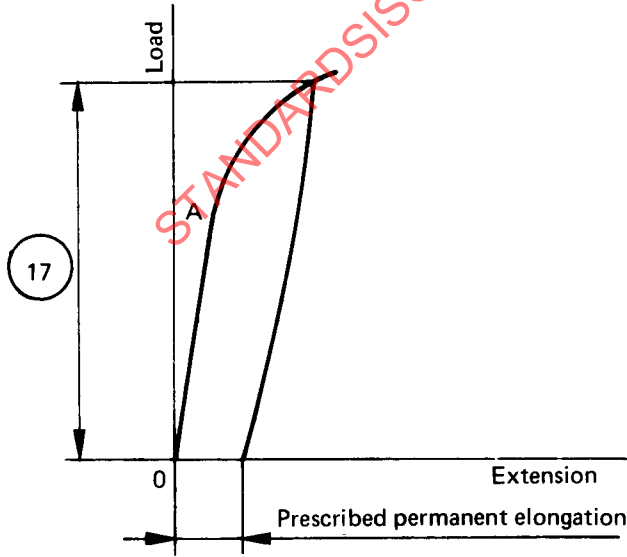


FIGURE 9

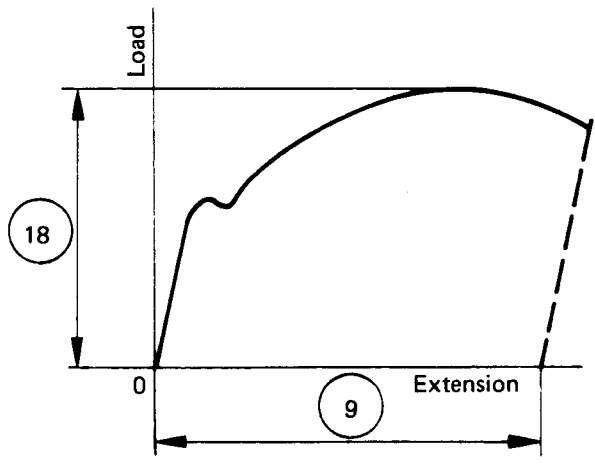


FIGURE 10

- A = Elastic limit
- B = Upper yield stress
- BCD = Yield stress elongation

6 TEST PIECES

6.1 General

The test piece may consist of a piece of the tube tested in full section or a longitudinal strip of full thickness cut from the tube. Preferably the tube should be tested in full section. The type of test piece is to be stated in the test report.

6.2 Full sections

Tubes to be tested in full section may be plugged at each end. The free length between the end of each plug and the nearest gauge mark shall be between $D/4$ and D . For arbitration purposes and provided that there is sufficient material, a value of D shall be used.

6.3 Longitudinal strips

The test piece shall have a parallel length, and may have enlarged ends, in which case there shall be a transition curve between the gripped ends and the parallel length. The parallel length L_c shall be between $L_o + b/2$ and $L_o + 2b$. For arbitration purposes and provided that there is sufficient material, $L_o + 2b$ shall be used.

The tolerance on form, i.e. variation over the gauge length, for test pieces cut from tubes is 0,33 mm.

6.4 Proportional test pieces

In order to obtain meaningful values of elongation it is preferable that the test pieces should have a specified relationship between gauge length and cross-sectional area. These are known as proportional test pieces. By international agreement this relationship has been established as $L_o = 5,65 \sqrt{S_o}$. If agreed by the materials standard, the elongation may be measured on a fixed gauge length and converted to a proportional gauge length by means of a formula or conversion chart. (See also 18.2.)

7 DETERMINATION OF CROSS-SECTIONAL AREA

The cross-sectional area of the test piece shall be determined to an accuracy of 1 %, unless otherwise specified in the specification for the material.

7.1 The cross-sectional area of a test piece consisting of a piece of tube in full section or of a longitudinal strip cut from the tube may be calculated from the mass of the measured length of the test piece. (ISO/R 336 gives the information that the mass per unit volume for carbon and low alloy steels should be taken as 7,85 Mg/m³ (490 lb/ft³). This value should be multiplied by 1,015 for austenitic stainless steels and by 0,985 for ferritic stainless steels.)

7.2 Alternatively, for tubes of regular cross-section, the cross-sectional area may be determined by linear measurement and calculation.

7.3 The cross-sectional area of a test piece consisting of a longitudinal strip cut from a tube shall be determined as follows :

$$S_o = ab$$

or (for test pieces with parallel sides)

$$S_o = ab \left[1 + \frac{b^2}{6D(D-2a)} \right]$$

8 MARKING THE ORIGINAL GAUGE LENGTH

8.1 For proportional test pieces, the value of L_o calculated in accordance with clause 6 can be rounded off to the nearest multiple of 5 mm (0.2 in) provided that the difference between the calculated and marked gauge length is less than 10 % of L_o .

8.2 Each end of the gauge length may be marked by means of a fine mark or a scribed line. An alternative method is first to paint the test piece with a quick-drying ink, and then to mark the gauge length by fine scribed lines. Incised markings are not recommended for notch-sensitive material as premature failure may occur at such a marking.

8.3 It may be useful to mark on the surface of a test piece a line parallel to the longitudinal axis. For test pieces with flat faces the line shall be at the middle of one of the wider faces.

8.4 If the parallel length is much in excess of the gauge length, as for instance with an unmachined test piece, a series of overlapping gauge lengths, some extending into the gripped portions, shall be marked on the bar.

9 METHOD OF GRIPPING

9.1 Test pieces shall be held by suitable means, for example wedges, screwed holders, shouldered holders, etc., as most convenient.

9.1.1 For tests on tube in full section, the length of the plug projecting beyond the grip in the direction of the gauge length shall not exceed the external diameter of the tube, and the shape shall be such that it does not interfere with the free elongation of the gauge length.

9.1.2 For tests on longitudinal strip, the parallel length shall not be flattened, but the gripped ends may be flattened for gripping in the testing machine.

9.2 Every endeavour must be made to ensure that test pieces are held in such a way that the load is applied as axially as possible. This is of particular importance when testing brittle material or when determining proof stress or yield stress.

10 ACCURACY OF TESTING EQUIPMENT

10.1 The testing machine shall be calibrated in accordance with ISO/R 147, and shall be maintained to grade 1,0 except when grade 0,5 is required by the standard for the material.

10.2 Where appropriate (see also 12.2), the apparent elastic compliance (K) of the tensile testing system shall be determined in accordance with ISO 2573.

10.3 The instrument error of an extensometer or proof stress indicator shall not exceed 5 % of the value of the elongation for which the stress value is obtained.

11 DETERMINATION OF PROPERTIES

The appropriate properties to be determined are to be stated in the specification for the material and determined in accordance with the procedures described in clauses 12 to 19.

NOTE — Attention is drawn to 4.9, 4.10 and 4.11 regarding the appropriate yield stresses and proof stresses to be stated.

12 TESTING TECHNIQUES

12.1 Factors affecting the rate of straining

It is necessary to take into account the wide variation of actual strain rate which can occur during a tensile test and which may affect the results obtained. The rate of straining during plastic deformation may be measured directly if suitable equipment is available. However, for most practical purposes the straining rate may be assessed in terms of loading rate, taking into account the following factors :

- 1) the apparent elastic compliance (K) of the testing machine and test piece assembly (see 12.3);
- 2) the area of cross-section of the test piece;
- 3) the parallel length of the test piece.

The first of these factors has to be established before testing.

12.2 Determination of testing system characteristics

The value of K is to be determined in accordance with ISO 2573. The value thereby obtained on the type of test piece normally used can be regarded as applicable to all tensile tests performed in the testing machine using the same type of attachments and under generally similar testing conditions.

12.3 Application of K

12.3.1 Measurement of upper and lower yield stress

For the measurement of upper and lower yield stress, a rate

of strain during plastic deformation not exceeding 0,002 5/s is recommended.

In addition to the recommended rate of straining, an upper limit of 30 N/mm²·s (1.9 tonf/in²·s) on the elastic stress rate is imposed to avoid, among other things, errors due to inertia effects.

Tables 1 and 2 give the values of the maximum permitted initial stress rate for different test pieces and different K -values for use when the required strain rate (not exceeding 0,002 5/s) cannot be achieved by direct control. A stressing rate not less than one-tenth of the elastic stressing rate determined from tables 1 and 2 is permitted. This will result in a slightly lower value of yield stress being obtained.

In those cases where the K -value of the tensile testing system cannot be determined in accordance with ISO 2573, a K -value of 0,000 3 mm/N may be used subject to agreement between the interested parties.

NOTE — A "hard" machine having a low K -value will permit a larger range of test piece cross-sectional areas to be tested at the maximum permitted elastic stressing rate without exceeding the straining rate of 0,002 5/s.

12.3.2 Measurement of proof stress

When a yield phenomenon is not present the strain rate imposed on the test piece in the vicinity of the proof stress may not be markedly dependent upon the value of K or the dimensions of the test piece. In proof stress determination a single maximum rate of application of stress of 30 N/mm²·s (1.9 tonf/in²·s) is, therefore, recommended.

13 OBSERVATIONS ON LOAD/EXTENSION DIAGRAMS

13.1 One of a variety of diagrams may be produced (for example figures 5 to 9). For many materials the initial part of such a load/extension diagram is straight (OA of figures 5 to 9). (Observations of extension made at a sequence of increasing loads during a tensile test may be used to derive corresponding values of stress and strain.)

13.2 As the load increases beyond point A in figure 5, the relationship between load and extension ceases to be linear. In some cases the load may attain a maximum, then decrease and remain sensibly constant while the extension increases markedly (BCD of figure 5). In other cases a maximum value is not obtained initially at the point where plastic deformation commences, and in such cases the level remains sensibly constant during yield while the extension increases markedly (CD of figure 6, curve X).

13.3 After yield is completed, further extension results only from increase in load.

13.4 Where the material does not show the yield type phenomenon, the extension will continue to increase non-proportionally to load after point A in figures 7, 8 and

9 has been reached. In such cases a proof stress or a permanent set stress should be measured (see clauses 15 and 16).

14 DETERMINATION OF YIELD STRESSES (YIELD POINTS)

14.1 The upper yield stress, R_{eH} , and/or lower yield stress, R_{eL} , may be determined visually or by a load/extension diagram or by similar means.

NOTE — When recording a load/extension diagram, it is permissible to record extension from the cross-head motion.

14.2 When determining these yield stresses, the test piece shall be loaded so that the strain rate is controlled in accordance with the following conditions :

14.2.1 The rate of strain of the parallel length of the test piece at the time of yielding shall not exceed 0,002 5/s. If this rate of straining cannot be controlled directly, it shall be controlled by regulating the rate of loading just before yield commences. The controls of the testing machine shall not be adjusted after 90 % of the expected yield load has been reached.

14.2.2 The maximum value of the initial stressing rate to be used for test pieces of different dimensions and in testing machines of different elastic compliances is stated in tables 1 and 2. See also note 4 to tables 1 and 2.

14.2.3 Under no circumstances shall the elastic stress rate exceed 30 N/mm²·s (1.9 tonf/in²·s).

14.3 In cases where the upper and lower yield stresses as defined in 4.9 cannot be easily determined (see figure 6, curve Y), a 0,5 % total elongation proof stress (proof stress under load) may be determined and regarded as the value of lower yield stress if so permitted by the material specification or agreed between the interested parties.

15 DETERMINATION OF PROOF STRESSES (YIELD STRENGTHS)

15.1 For the determination of proof stress (non-proportional elongation), R_p , or proof stress (total elongation), R_t , the rate of application of stress in the elastic range shall not exceed 30 N/mm²·s (1.9 tonf/in²·s) — see 12.3.2 — and may be within the range 3 to 30 N/mm²·s. For both methods an extensometer shall be used.

15.2 Proof stress (non-proportional elongation) (R_p) is determined from a load/extension diagram on which a line is drawn parallel to the straight portion of the curve and distant from it by the required non-proportional amount, for example 0,2 %. The point at which the line cuts the curve represents the required proof stress. (See figure 7.)

15.2.1 Accurate determination of the load/extension diagram is necessary (see 10.3). The curve may be obtained by either automatic or manual methods. However, the use of a proof stress indicator without the production of a load/extension diagram is permitted.

15.2.2 The required percentage elongation at which a proof stress is to be determined shall be stated in the specification for the material.

15.3 Proof stress (total elongation) (R_t) is illustrated in the load/extension diagram shown in figure 8 on which a line is drawn parallel to the γ -axis of the diagram and distant from it by the required total elongation. The load at which the extensometer indicates the total elongation required represents the required proof stress.

15.3.1 If permitted by the material specification or agreed between the interested parties, dividers may be used to measure the total elongation when proof stress R_t is specified.

15.3.2 The required total elongation at which the proof stress is to be determined shall be stated in the specification for the material or agreed between the interested parties.

NOTE — For ferritic steels, where the specified value is not greater than 650 N/mm² (40 tonf/in²), the recommended value is 0,5 % unless otherwise stated. For values greater than 650 N/mm² (40 tonf/in²), this method is not valid unless the limiting total extension is increased.

For austenitic steels, the value to be taken is that stated in the standard for the material.

16 PROVING TESTS FOR PERMANENT SET STRESS

16.1 If a permanent set stress is specified or agreed, the small tensioning stress stated in the specification for the material shall be applied to the test piece. The stress is increased to the specified value and maintained for 10 to 15 s. It is then reduced below the initial tensioning stress and then increased to it.

16.2 It shall be verified that the gauge length, when measured with an extensometer, has not acquired a permanent extension greater than the specified percentage of the extensometer gauge length.

17 DETERMINATION OF TENSILE STRENGTH

17.1 When determining tensile strength (see figure 10), the test piece shall be loaded in accordance with the following conditions unless stated otherwise in the standard for the material :

17.1.1 In the plastic range, the rate of separation of the cross-heads of the testing machine, expressed as a

percentage of the parallel length per minute, shall at any moment be not greater than twice the specified minimum elongation plus 10.

17.1.2 If the yield or proof stress is not to be determined, the range within the elastic range may be as high as that permitted in the plastic range.

17.1.3 In all cases, the speed of testing shall be as uniform as possible and the change of speed from the elastic to the plastic range shall be made gradually and without shock.

17.2 The tensile strength is to be determined in accordance with the definition given in 4.8.

18 DETERMINATION OF PERCENTAGE ELONGATION AFTER FRACTURE

18.1 The percentage elongation after fracture shall be determined in accordance with the definition given in 4.4 and expressed to the nearest 1 %.

18.2 Any statement of the results of a percentage elongation test shall include the dimensions of the section of the test piece and its gauge length.

NOTE — Where it is convenient, for economic or other reasons, to use a fixed gauge length irrespective of the cross-sectional area, the equivalent elongation on $5,65 \sqrt{S_0}$ may, if required, be obtained by means of a formula or conversion chart agreed between the interested parties, for example ISO 2566. In cases of dispute, the elongation shall be measured on a gauge length of $5,65 \sqrt{S_0}$.

18.3 The full value of the percentage elongation may not be obtained unless fracture of the test piece has occurred at

a section situated between the gauge marks, and at a sufficient distance from the nearest gauge mark. Care must be taken to ensure proper contact between the broken parts of the test piece when measuring the final length between gauge marks (see 18.5). This is of particular importance when measuring test pieces of small cross-section and test pieces having low elongation values. For ease of measurement a simple jig may be used which will enable the broken pieces to be mated axially at the original point of fracture.

18.4 If the specified minimum elongation is less than 5 %, it is recommended that special precautions in the determination of the elongation be employed.

18.5 In acceptance testing, the test results are regarded as valid, irrespective of the position of the fracture, provided that the minimum elongation specified has been obtained. If the minimum elongation specified is not obtained, the results of a test should, unless otherwise agreed, be discarded if the distance between the fracture and the nearer gauge mark is less than one-third of the gauge length.

19 DETERMINATION OF PERCENTAGE REDUCTION OF AREA

19.1 The determination of percentage reduction of area is difficult or impracticable in the case of full section tubes or of strips cut from very thin wall tubes and therefore not required for these forms of test piece.

19.2 Where practicable, the percentage reduction of area is to be determined in accordance with the definition given in 4.5.

TABLE 1 — Values of initial rate of application of stress for determination of yield stress (SI units)
(to be used when the required plastic strain rate — not exceeding 0,002 5/s — cannot be achieved by direct control)

Test piece dimensions		Maximum elastic stress rate, N/mm ² · s													
L _c	S ₀	Apparent elastic compliance, K, mm/N =													
mm	mm ²	0,000 02	0,000 04	0,000 06	0,000 08	0,000 10	0,000 15	0,000 20	0,000 25	0,000 30	0,000 35	0,000 40	0,000 45	0,000 50	
62,5	250	29,5	15,2	10,2	7,7	6,2	4,1	3,1	2,5	2,1	1,8	1,6	1,2	1,2	
	200		18,8	12,7	9,6	7,7	5,2	3,9	3,1	2,6	2,2	1,9	1,7	1,6	
	150		24,8	16,8	12,7	10,2	6,9	5,2	4,1	3,4	3,0	2,6	2,3	2,1	
	100			24,8	18,8	15,2	10,2	7,7	6,2	5,2	4,4	3,9	3,4	3,1	
	80				23,3	18,8	12,7	9,6	7,7	6,4	5,5	4,8	4,3	3,9	
75	60	Note 3	30			24,8	16,8	12,7	10,2	8,5	7,3	6,4	5,7	5,2	
	40						24,8	18,8	15,2	12,7	10,9	9,6	8,5	7,7	
	250		18,1	12,2	9,2	7,4	5,0	3,7	3,0	2,5	2,1	1,9	1,7	1,5	
	200		22,4	15,2	11,5	9,2	6,2	4,6	3,7	3,1	2,7	2,3	2,1	1,9	
	150		29,5	20,0	15,2	12,2	8,2	6,2	5,0	4,1	3,5	3,1	2,8	2,5	
125	100			29,5	22,4	18,1	12,2	9,2	7,4	6,2	5,3	4,6	4,1	3,7	
	80		30		27,7	22,4	15,2	11,5	9,2	7,7	6,6	5,8	5,2	4,6	
	60	Note 3				29,5	20,0	15,2	12,2	10,2	8,8	7,7	6,9	6,2	
	40						29,5	22,4	18,1	15,2	13,1	11,5	10,2	9,2	
			29,5	20,0	15,2	12,2	8,2	6,2	5,0	4,1	3,5	3,1	2,8	2,5	
225	250			24,8	18,8	15,2	10,2	7,7	6,2	5,2	4,4	3,9	3,4	3,1	
	200				24,8	20,0	13,5	10,2	8,2	6,9	5,9	5,2	4,6	4,1	
	150					29,5	20,0	15,2	12,2	10,2	8,9	7,7	6,9	6,2	
	100	Note 3	30				24,8	18,8	15,2	12,7	10,9	9,6	8,5	7,7	
	80							24,8	20,0	16,8	14,5	12,7	11,3	10,2	
325	400								29,5	24,8	21,4	18,8	16,8	15,2	
	300														
	250														
	800		17,0	11,5	8,6	6,9	4,6	3,5	2,8	2,3	2,0	1,8	1,6	1,4	
	700		19,3	13,1	9,9	7,9	5,3	4,0	3,2	2,7	2,3	2,0	1,8	1,6	
300	600		22,0	15,2	11,5	9,2	6,2	4,6	3,7	3,1	2,7	2,3	2,1	1,9	
	500		26,7	18,1	13,7	11,0	7,4	5,6	4,5	3,7	3,2	2,8	2,5	2,2	
	400			22,4	17,0	13,7	9,2	6,9	5,6	4,6	4,0	3,5	3,1	2,8	
	300		30	29,5	22,4	18,1	12,2	9,2	7,4	6,2	5,3	4,6	4,1	3,7	
	250				26,7	21,6	14,5	11,0	8,8	7,4	6,4	5,6	5,0	4,5	
300	2 000		10,0	6,7	5,0	4,0	2,7	2,0	1,6	1,4	1,2	1,0	0,9	0,8	
	1 500		13,2	8,9	6,1	5,4	3,6	2,7	2,2	1,8	1,5	1,4	1,2	1,1	
	1 250		15,8	10,6	8,0	6,4	4,3	3,2	2,6	2,2	1,9	1,6	1,4	1,3	
	1 000		19,6	13,2	10,0	8,0	5,4	4,0	3,2	2,7	2,3	2,0	1,8	1,6	
	800		24,2	16,4	12,4	10,0	6,7	5,0	4,0	3,7	2,9	2,5	2,2	2,0	
300	600			21,6	16,4	13,2	8,9	6,7	5,4	4,5	3,8	3,4	3,0	2,7	
	400				24,2	19,6	13,2	10,0	8,0	6,7	5,7	5,0	4,5	4,0	
	300		30			25,6	17,5	13,2	10,6	8,9	7,6	6,7	6,0	5,4	